

β -V₂N ($L'3_2$) Structure: AB2_hP9_162_ad_k-001


This structure previously used the label(s) **AB2_hP9_162_ad_k**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/RBZR>

https://aflow.org/prototype-encyclopedia/AB2_hP9_162_ad_k-001

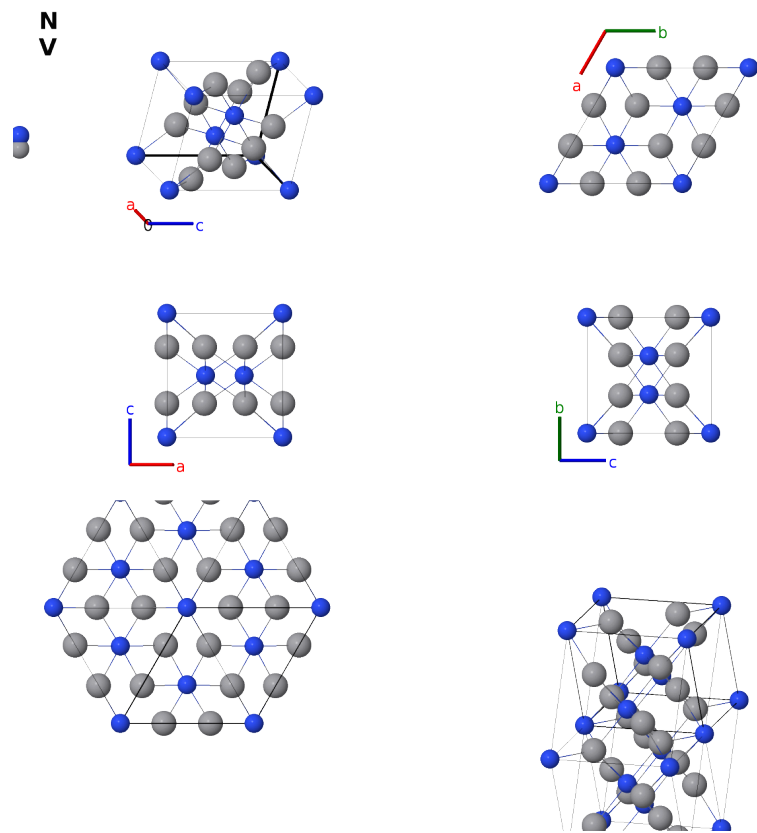

Prototype	NV ₂
AFLOW prototype label	AB2_hP9_162_ad_k-001
<i>Strukturbericht</i> designation	$L'3_2$
ICSD	8236
CCDC	1594017
Pearson symbol	hP9
Space group number	162
Space group symbol	$P\bar{3}1m$


AFLOW prototype command `aflow --proto=AB2_hP9_162_ad_k-001`
 `--params=a, c/a, x3, z3`

Other compounds with this structure

Cr₂N, ϵ -Fe₂N, Mo₂C, Nb₂C, β -Nb₂N, β -Ta₂N, W₂C

- (Parthé, 1993) is the only reference we have seen with a $L'3_2$ *Strukturbericht* designation.
- (Christensen, 1979) states that ϵ -Fe₂N is the prototype for this structure. We will instead follow (Villars, 1991) and the ICSD, which use β -V₂N as the prototype.
- The ternary version of this structure is rosiaite, PbSb₂O₆.

Trigonal (Hexagonal) primitive vectors
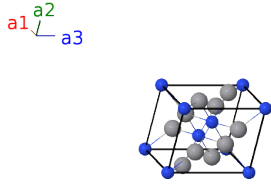
$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}} \end{aligned}$$


Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	= 0	=	0	(1a)	N I
$\mathbf{B}_2$	= $\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(2d)	N II
$\mathbf{B}_3$	= $\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(2d)	N II
$\mathbf{B}_4$	= $x_3 \mathbf{a}_1 + z_3 \mathbf{a}_3$	=	$\frac{1}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(6k)	V I
$\mathbf{B}_5$	= $x_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$\frac{1}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(6k)	V I
$\mathbf{B}_6$	= $-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$-ax_3 \hat{\mathbf{x}} + cz_3 \hat{\mathbf{z}}$	(6k)	V I
$\mathbf{B}_7$	= $-x_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-\frac{1}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(6k)	V I
$\mathbf{B}_8$	= $-x_3 \mathbf{a}_1 - z_3 \mathbf{a}_3$	=	$-\frac{1}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(6k)	V I
$\mathbf{B}_9$	= $x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$ax_3 \hat{\mathbf{x}} - cz_3 \hat{\mathbf{z}}$	(6k)	V I

References

- [1] A. N. Christensen and B. Lebech, *The structure of β -Vanadium Nitride*, Acta Crystallogr. Sect. B **35**, 2677–2678 (1979), doi:10.1107/S0567740879010141.
- [2] E. Parthé, L. Gelato, B. Chabot, M. Penso, K. Cenzula, and R. Gladyshevskii, *Standardized Data and Crystal Chemical Characterization of Inorganic Structure Types, Gmelin Handbook of Inorganic and Organometallic Chemistry*, vol. 2 (Springer-Verlag, Berlin, Heidelberg, 1993), 8 edn., doi:10.1007/978-3-662-02909-1_3.
- [3] P. Villars and L. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases* (ASM International, Materials Park, OH, 1991), 2nd edn.

Found in

- [1] P. Villars and L. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases* (ASM International, Materials Park, OH, 1991), 2nd edn.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017