

Rhombohedral MoS₂ Structure:


AB2_hR3_160_a_2a-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/EW06>

https://aflow.org/prototype-encyclopedia/AB2_hR3_160_a_2a-001

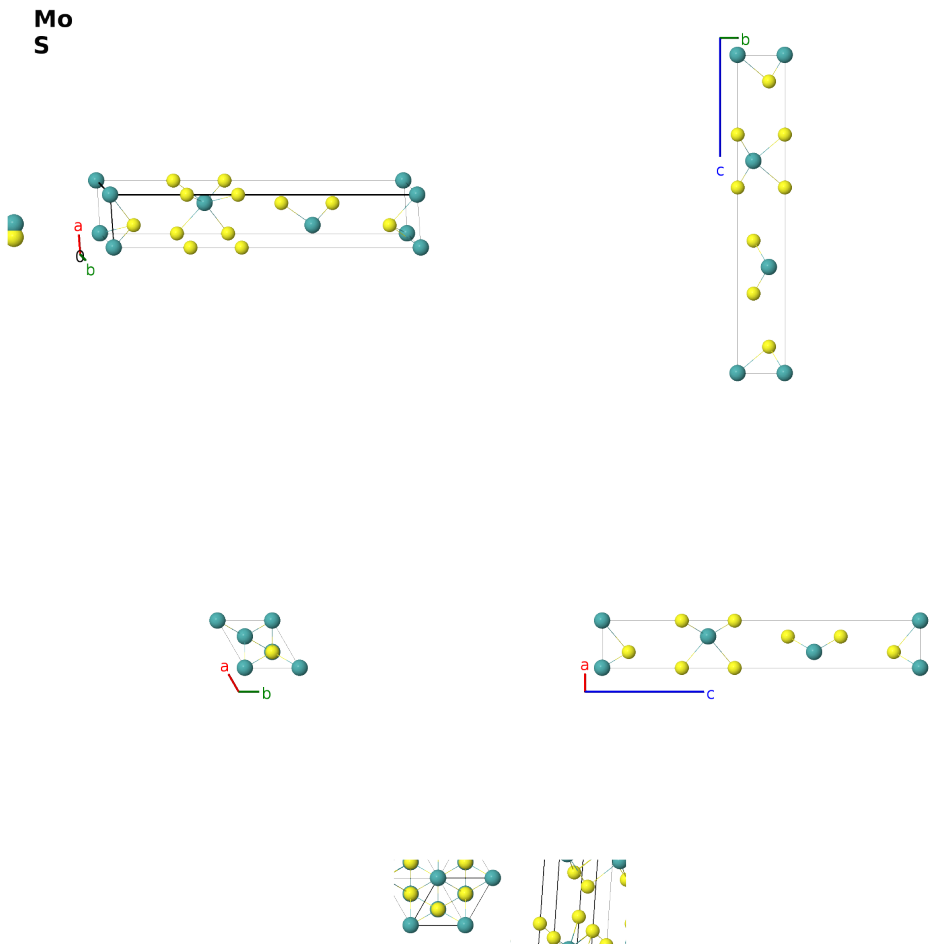

Prototype	MoS ₂
AFLOW prototype label	AB2_hR3_160_a_2a-001
ICSD	43695
CCDC	1613167
Pearson symbol	hR3
Space group number	160
Space group symbol	$R\bar{3}m$

AFLOW prototype command `aflow --proto=AB2_hR3_160_a_2a-001`
 `--params=a, c/a, x1, x2, x3`


Other compounds with this structure

MoN₂, NbS₂, NbSe₂, TaS₂, TaSe₂, WS₂

- MoS₂ exists naturally in two forms: this rhombohedral structure, and the the hexagonal structure, molybdenite, *Strukturbericht C7*. The two structures differ due to the stacking of the MoS₂ layers.
 - Depending on the preparation method, MoS₂ can exist in other forms, including a trigonal structure.
 - Hexagonal settings of this structure can be obtained with the option `--hex`.
-

Rhombohedral primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{\sqrt{3}}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= -\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \end{aligned}$$

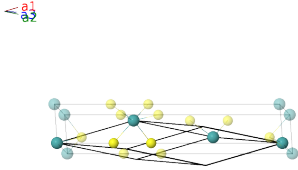

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	$x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + x_1 \mathbf{a}_3$	$=$	$cx_1 \hat{\mathbf{z}}$	(1a) Mo I
$\mathbf{B}_2$	$=$	$x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$cx_2 \hat{\mathbf{z}}$	(1a) S I
$\mathbf{B}_3$	$=$	$x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$cx_3 \hat{\mathbf{z}}$	(1a) S II

References

[1] F. Jellinek, G. Brauer, and H. Müller, *Molybdenum and Niobium Sulphides*, Nature **185**, 376–377 (1960), doi:10.1038/185376a0.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.