

HoSb₂ Structure:

AB2_oC6_21_a_k-002


This structure previously used the label(s) **AB2_oC6_21_a_k.HoS_b2**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/DD5U>

https://aflow.org/prototype-encyclopedia/AB2_oC6_21_a_k-002

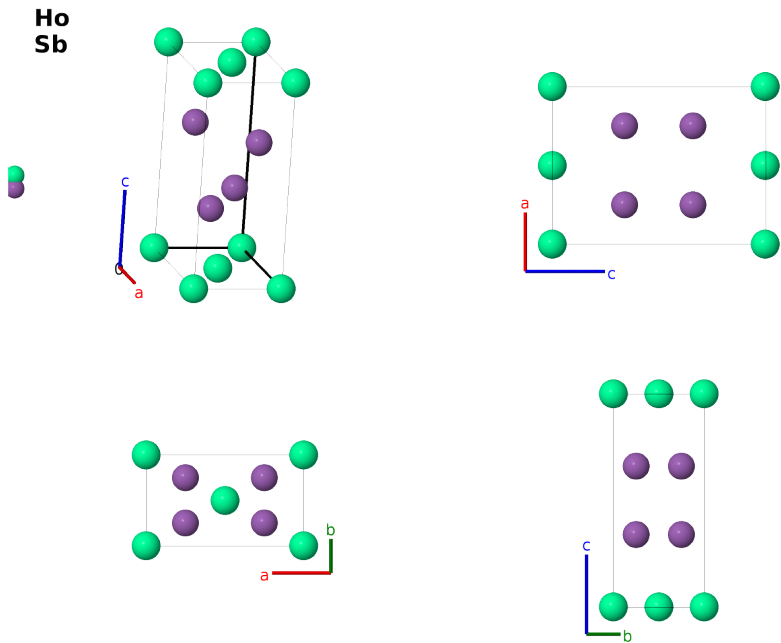

Prototype	HoSb ₂
AFLOW prototype label	AB2_oC6_21_a_k-002
ICSD	26220
CCDC	1601649
Pearson symbol	oC6
Space group number	21
Space group symbol	C222
AFLOW prototype command	<code>aflow --proto=AB2_oC6_21_a_k-002 --params=a, b/a, c/a, z₂</code>


Other compounds with this structure

LuSb₂, YSb₂, DySb₂ (HT), GdSb₂ (HT), TbSb₂ (HT)

- Measurements were performed at a pressure of 65 kBar
- The primitive unit cell is nearly hexagonal
- The author states “We are well aware of the fact that the structure presented here may indeed be only a subcell of the true structure.”
- HoSb₂ and Ta₂H share the same AFLOW prototype label, AB2_oC6_21_a_k. The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Base-centered Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{2}b\hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}b\hat{\mathbf{y}} \\ \mathbf{a}_3 &= c\hat{\mathbf{z}}\end{aligned}$$

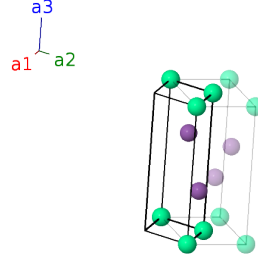

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(2a) Ho I
$\mathbf{B}_2$	$=$	$\frac{1}{2}\mathbf{a}_2 + z_2\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + cz_2\hat{\mathbf{z}}$	(4k) Sb I
$\mathbf{B}_3$	$=$	$\frac{1}{2}\mathbf{a}_1 - z_2\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} - \frac{1}{4}b\hat{\mathbf{y}} - cz_2\hat{\mathbf{z}}$	(4k) Sb I

References

- [1] Q. Johnson, *The Crystal Structure of High-Pressure Synthesized Holmium Diantimonde*, Inorg. Chem. **10**, 2089–2090 (1971), doi:10.1021/ic50103a059.

Found in

- [1] M. N. Abdusaljamov, O. R. Burnashev, and K. E. Mironov, *The Ho-Sb Alloy System*, J. Less-Common Met. **102**, L19–L22 (1984), doi:10.1016/0022-5088(84)90403-X.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.