

Hydrophilite (CaCl₂, C35) Structure: AB2_oP6_58_a_g-001


This structure previously used the label(s) **AB2_oP6_58_a_g.CaCl2**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/YTPF>

https://aflow.org/prototype-encyclopedia/AB2_oP6_58_a_g-001

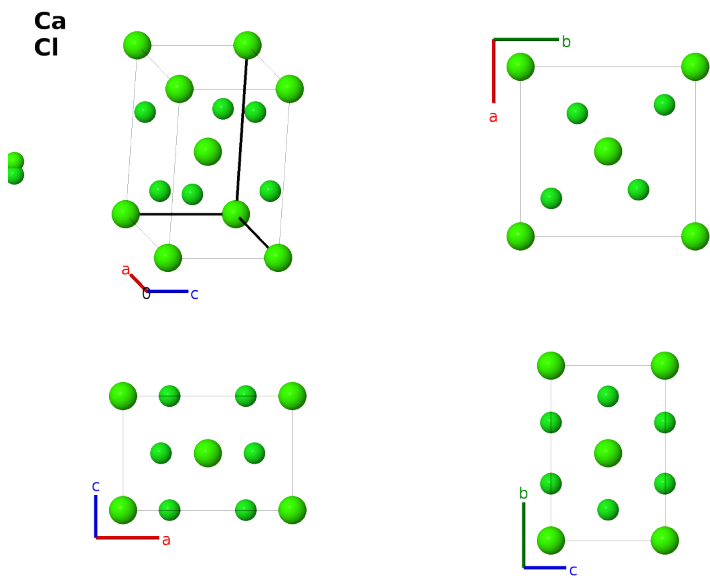


Prototype	CaCl ₂
AFLOW prototype label	AB2_oP6_58_a_g-001
<i>Strukturbericht</i> designation	C35
Mineral name	hydrophilite
ICSD	26686
CCDC	1602076
Pearson symbol	oP6
Space group number	58
Space group symbol	<i>Pnnm</i>
AFLOW prototype command	<code>aflow --proto=AB2_oP6_58_a_g-001 --params=a, b/a, c/a, x₂, y₂</code>

Other compounds with this structure

BeF₂, CaBr₂, CaCl₂, Co₂C, CrCl₂, Co₂N, CrO₂, MgF₂, FeO₂, GeO₂, MgF₂, MnF₂, MnO₂, NiF₂, PbO₂, PtGe₂, PtO₂, RuO₂, SiO₂, SnO₂, VO₂, YbBr₂, ZrO₂

- Hydrophilite (CaCl₂, *C*35), η -Fe₂C, and marcasite (FeS₂, *C*18) have the same AFLOW prototype label, AB2_oP6_58_a-g. They are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors

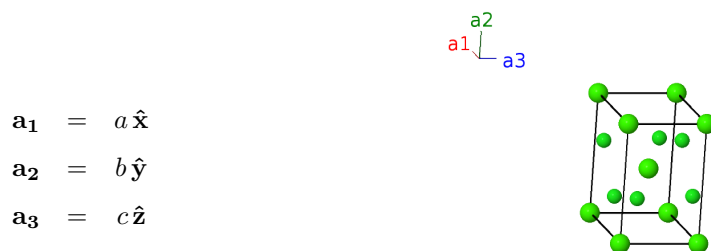

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= 0$	$=$	0	(2a)	Ca I
$\mathbf{B}_2$	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} b \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(2a)	Ca I
$\mathbf{B}_3$	$= x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2$	$=$	$ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}}$	(4g)	Cl I
$\mathbf{B}_4$	$= -x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2$	$=$	$-ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}}$	(4g)	Cl I
$\mathbf{B}_5$	$= -\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_2 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} + b\left(y_2 + \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(4g)	Cl I
$\mathbf{B}_6$	$= \left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 - \left(y_2 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} - b\left(y_2 - \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(4g)	Cl I

References

- [1] A. van Bever and W. Nieuwenkamp, *Die Kristallstruktur von Calciumchlorid, CaCl₂*, Z. Kristallogr. **90**, 374–376 (1935), doi:10.1524/zkri.1935.90.1.374.

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017