


LaRu₃Si₂ Structure: AB3C2_hP12_176_b_h_f-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/JSY8>

https://aflow.org/prototype-encyclopedia/AB3C2_hP12_176_b_h_f-001

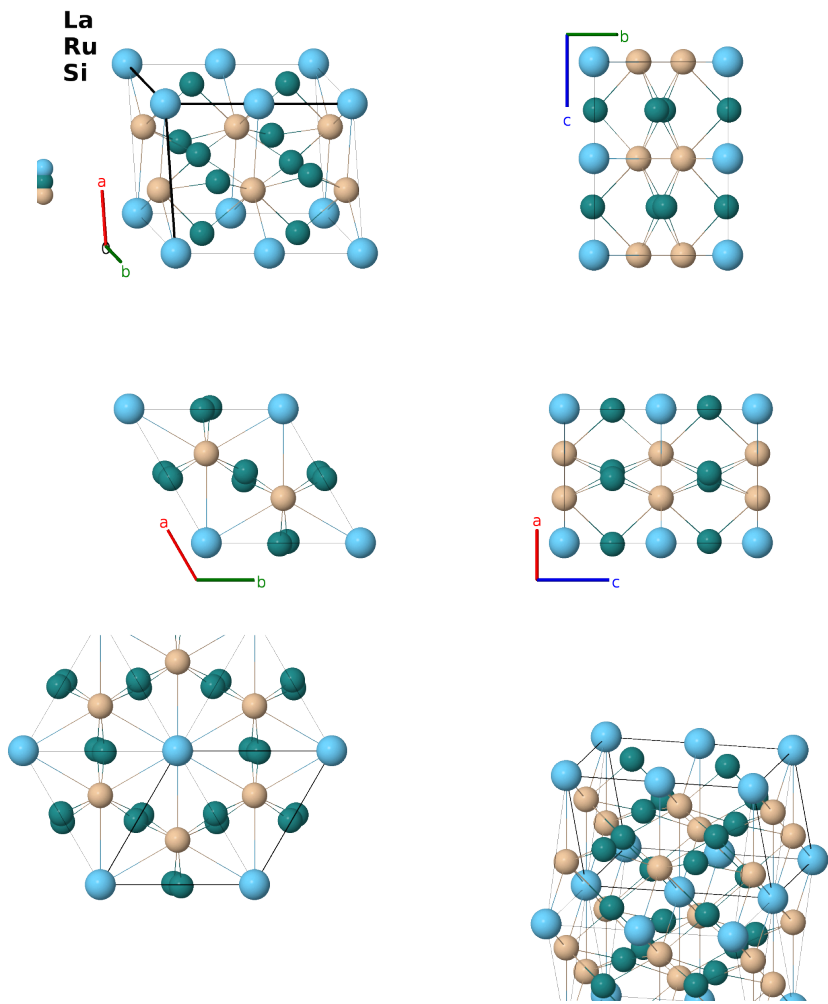

Prototype	LaRu ₃ Si ₂
AFLOW prototype label	AB3C2_hP12_176_b_h_f-001
ICSD	100785
CCDC	1659890
Pearson symbol	hP12
Space group number	176

Space group symbol $P6_3/m$

AFLOW prototype command `aflow --proto=AB3C2_hP12_176_b_h_f-001`
`--params=a, c/a, z2, x3, y3`


Other compounds with this structure

CeRu₃Si₂, NdRu₃Si₂, ThRu₃Si₂, YRu₃Si₂

- (Vandenberg, 1980) give the coordinates $z_2 \approx 0$ (Si) and $x_3 \approx 1/2, y_3 \approx 0$ (Ru). Using these values would make the space group $P6/mmm$ #191, with the unit cell half the size of the correct cell. Accordingly we offset these coordinates slightly, keeping the distances between atoms consistent with the values given by (Vandenberg, 1980).

Hexagonal primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}} \end{aligned}$$

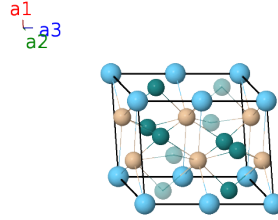

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= 0$	$=$	0	(2b)	La I
$\mathbf{B}_2$	$= \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}c \hat{\mathbf{z}}$	(2b)	La I
$\mathbf{B}_3$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4f)	Si I
$\mathbf{B}_4$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4f)	Si I
$\mathbf{B}_5$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4f)	Si I
$\mathbf{B}_6$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4f)	Si I
$\mathbf{B}_7$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_3 + y_3) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a(x_3 - y_3) \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Ru I
$\mathbf{B}_8$	$= -y_3 \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_3 - 2y_3) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Ru I
$\mathbf{B}_9$	$= -(x_3 - y_3) \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(2x_3 - y_3) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ay_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Ru I
$\mathbf{B}_{10}$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_3 + y_3) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a(x_3 - y_3) \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Ru I
$\mathbf{B}_{11}$	$= y_3 \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(-x_3 + 2y_3) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Ru I
$\mathbf{B}_{12}$	$= (x_3 - y_3) \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(2x_3 - y_3) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ay_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Ru I

References

- [1] J. M. Vandenberg and H. Barz, *The crystal structure of a new ternary silicide in the system rare-earth-ruthenium-silicon*, Mater. Res. Bull. **15**, 1493–1498 (1980), doi:10.1016/0025-5408(80)90108-7.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.