

# Lu<sub>2</sub>CoGa<sub>3</sub> Structure: AB3C2\_hP24\_194\_f\_k\_bh-001


This structure previously used the label(s) **AB3C2\_hP24\_194\_f\_k\_bh**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/0GA4>

[https://aflow.org/prototype-encyclopedia/AB3C2\\_hP24\\_194\\_f\\_k\\_bh-001](https://aflow.org/prototype-encyclopedia/AB3C2_hP24_194_f_k_bh-001)

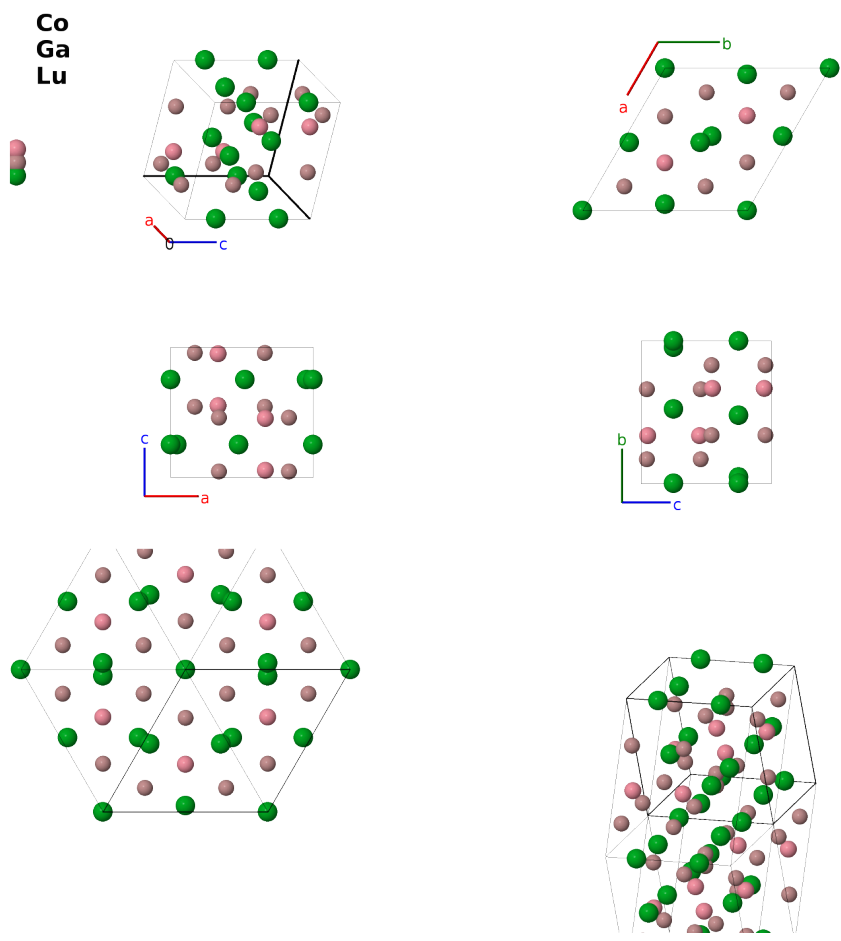

|                       |                                   |
|-----------------------|-----------------------------------|
| Prototype             | CoGa <sub>3</sub> Lu <sub>2</sub> |
| AFLOW prototype label | AB3C2_hP24_194_f_k_bh-001         |
| ICSD                  | 300248                            |
| CCDC                  | 1723877                           |
| Pearson symbol        | hP24                              |
| Space group number    | 194                               |

Space group symbol  $P6_3/mmc$

AFLOW prototype command `aflow --proto=AB3C2_hP24_194_f_k_bh-001`  
`--params=a,c/a,z2,x3,x4,z4`


### Other compounds with this structure

Ce<sub>2</sub>RhSi<sub>3</sub>, Dy<sub>2</sub>CoGa<sub>3</sub>, Dy<sub>2</sub>RhSi<sub>3</sub>, Er<sub>2</sub>CoGa<sub>3</sub>, Er<sub>2</sub>RhSi<sub>3</sub>, Gd<sub>2</sub>PdSi<sub>3</sub>, Gd<sub>2</sub>RhSi<sub>3</sub>, Ho<sub>2</sub>CoGa<sub>3</sub>, Ho<sub>2</sub>RhSi<sub>3</sub>, La<sub>2</sub>RhSi<sub>3</sub>, Nd<sub>2</sub>PdSi<sub>3</sub>, Nd<sub>2</sub>RhSi<sub>3</sub>, Tb<sub>2</sub>CoGa<sub>3</sub>, Tb<sub>2</sub>RhSi<sub>3</sub>, Tm<sub>2</sub>CoGa<sub>3</sub>, Y<sub>2</sub>CoGa<sub>3</sub>, Y<sub>2</sub>RhSi<sub>3</sub>, Yb<sub>2</sub>CoGa<sub>3</sub>

- Although (Gladyshevskii, 1992) refers to these compounds as “new members of the AlB<sub>2</sub> structure family” and this structure is related to AlB<sub>2</sub>, the two are not isostructural.
- The original data was presented in (Gladyshevskii, 1986). We do not have a copy of that publication, so we use the data given in (Gladyshevskii, 1992).
- The ICSD entry for this paper is for the isostructural compound Er<sub>2</sub>RhSi<sub>3</sub>.
- This structure is closely related to what we call the Er<sub>2</sub>RhSi<sub>3</sub> structure, which lacks the inversion symmetry of this structure. See the discussion there and in (Gladyshevskii, 1992).

### Hexagonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

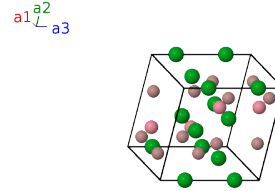

### Basis vectors

|                   | Lattice coordinates                                                                        |     | Cartesian coordinates                                                                                                 | Wyckoff position | Atom type |
|-------------------|--------------------------------------------------------------------------------------------|-----|-----------------------------------------------------------------------------------------------------------------------|------------------|-----------|
| $\mathbf{B}_1$    | $= \frac{1}{4} \mathbf{a}_3$                                                               | $=$ | $\frac{1}{4}c \hat{\mathbf{z}}$                                                                                       | (2b)             | Lu I      |
| $\mathbf{B}_2$    | $= \frac{3}{4} \mathbf{a}_3$                                                               | $=$ | $\frac{3}{4}c \hat{\mathbf{z}}$                                                                                       | (2b)             | Lu I      |
| $\mathbf{B}_3$    | $= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_2 \mathbf{a}_3$                 | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$                        | (4f)             | Co I      |
| $\mathbf{B}_4$    | $= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$ | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$        | (4f)             | Co I      |
| $\mathbf{B}_5$    | $= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_2 \mathbf{a}_3$                 | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$                        | (4f)             | Co I      |
| $\mathbf{B}_6$    | $= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$ | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$        | (4f)             | Co I      |
| $\mathbf{B}_7$    | $= x_3 \mathbf{a}_1 + 2x_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$                        | $=$ | $\frac{3}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$          | (6h)             | Lu II     |
| $\mathbf{B}_8$    | $= -2x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$                       | $=$ | $-\frac{3}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$         | (6h)             | Lu II     |
| $\mathbf{B}_9$    | $= x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$                         | $=$ | $-\sqrt{3}ax_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$                                                      | (6h)             | Lu II     |
| $\mathbf{B}_{10}$ | $= -x_3 \mathbf{a}_1 - 2x_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$                       | $=$ | $-\frac{3}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$         | (6h)             | Lu II     |
| $\mathbf{B}_{11}$ | $= 2x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$                        | $=$ | $\frac{3}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$          | (6h)             | Lu II     |
| $\mathbf{B}_{12}$ | $= -x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$                        | $=$ | $\sqrt{3}ax_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$                                                       | (6h)             | Lu II     |
| $\mathbf{B}_{13}$ | $= x_4 \mathbf{a}_1 + 2x_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$                                | $=$ | $\frac{3}{2}ax_4 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$                  | (12k)            | Ga I      |
| $\mathbf{B}_{14}$ | $= -2x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$                               | $=$ | $-\frac{3}{2}ax_4 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$                 | (12k)            | Ga I      |
| $\mathbf{B}_{15}$ | $= x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$                                 | $=$ | $-\sqrt{3}ax_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$                                                              | (12k)            | Ga I      |
| $\mathbf{B}_{16}$ | $= -x_4 \mathbf{a}_1 - 2x_4 \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$               | $=$ | $-\frac{3}{2}ax_4 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$ | (12k)            | Ga I      |

$$\begin{aligned}
\mathbf{B}_{17} &= 2x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3 &= \frac{3}{2}ax_4 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}} &(12k) &\text{Ga I} \\
\mathbf{B}_{18} &= -x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3 &= \sqrt{3}ax_4 \hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}} &(12k) &\text{Ga I} \\
\mathbf{B}_{19} &= 2x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 - z_4 \mathbf{a}_3 &= \frac{3}{2}ax_4 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}} &(12k) &\text{Ga I} \\
\mathbf{B}_{20} &= -x_4 \mathbf{a}_1 - 2x_4 \mathbf{a}_2 - z_4 \mathbf{a}_3 &= -\frac{3}{2}ax_4 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}} &(12k) &\text{Ga I} \\
\mathbf{B}_{21} &= -x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 - z_4 \mathbf{a}_3 &= \sqrt{3}ax_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}} &(12k) &\text{Ga I} \\
\mathbf{B}_{22} &= -2x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3 &= -\frac{3}{2}ax_4 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} - c\left(z_4 - \frac{1}{2}\right) \hat{\mathbf{z}} &(12k) &\text{Ga I} \\
\mathbf{B}_{23} &= x_4 \mathbf{a}_1 + 2x_4 \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3 &= \frac{3}{2}ax_4 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} - c\left(z_4 - \frac{1}{2}\right) \hat{\mathbf{z}} &(12k) &\text{Ga I} \\
\mathbf{B}_{24} &= x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3 &= -\sqrt{3}ax_4 \hat{\mathbf{y}} - c\left(z_4 - \frac{1}{2}\right) \hat{\mathbf{z}} &(12k) &\text{Ga I}
\end{aligned}$$

## References

- [1] R. E. Gladyshevskii, K. Cenxual, and E. Parthé, *Er<sub>2</sub>RhSi<sub>3</sub> and R<sub>2</sub>CoGa<sub>3</sub> (R = Y, Tb, Dy, Ho, Er, Tm, Yb) with Lu<sub>2</sub>CoGa<sub>3</sub> type structure: new members of the A1B2 structure family*, J. Am. Chem. Soc. **189**, 221–228 (1992), doi:10.1016/0925-8388(92)90711-H.
- [2] *Collected Abstracts* (1986). XI Ukrainian Republic Conference on Inorganic Chemistry, p. 49.

## First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.