

CuTaS₃ Structure:


AB3C_oP20_62_c_3c_c-002

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/S2FJ>

https://aflow.org/prototype-encyclopedia/AB3C_oP20_62_c_3c_c-002

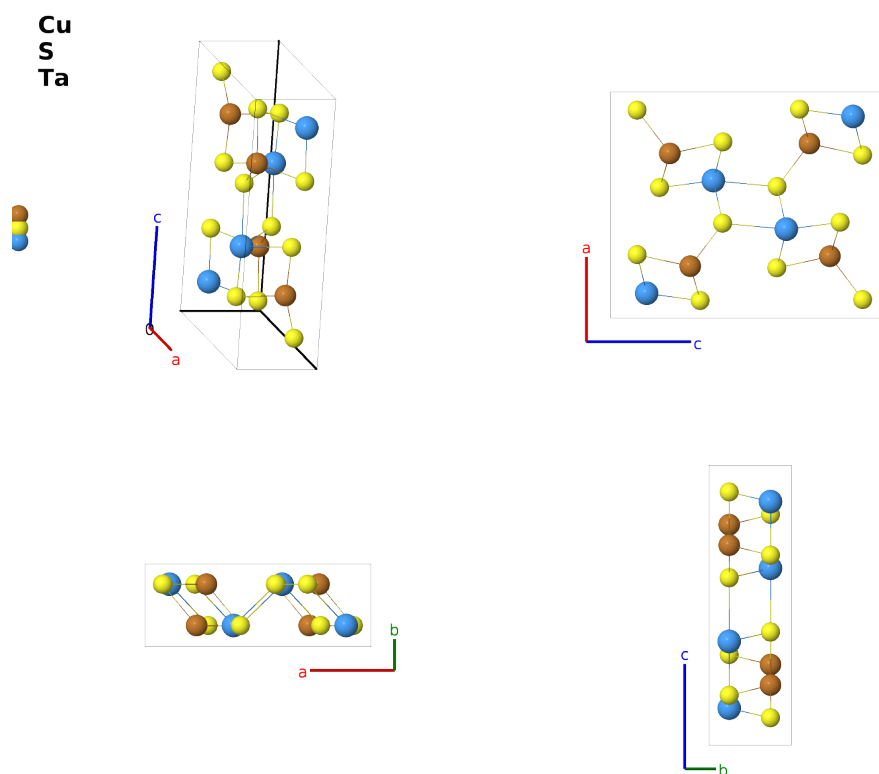

Prototype	CuS ₃ Ta
AFLOW prototype label	AB3C_oP20_62_c_3c_c-002
ICSD	62537
CCDC	1625765
Pearson symbol	oP20
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	<pre>aflow --proto=AB3C_oP20_62_c_3c_c-002 --params=a, b/a, c/a, x₁, z₁, x₂, z₂, x₃, z₃, x₄, z₄, x₅, z₅</pre>

Other compounds with this structure

LaCrS₃, CeCrS₃, SmCrS₃, NdCrS₃, CeCrSe₃, PbSnS₃, RbCdBr₃, RbCdCl₃, (Ti, Sn)₂S₃

- This structure has the same AFLOW label, AB3C_oP20_62_c_3c_c, as NH₄CdCl₃ (*E*2₄). The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	Cu I
$\mathbf{B}_2$	$= -(x_1 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Cu I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	Cu I
$\mathbf{B}_4$	$= (x_1 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Cu I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_6$	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_8$	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4c)	S II
$\mathbf{B}_{10}$	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	S II
$\mathbf{B}_{11}$	$= -x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4c)	S II
$\mathbf{B}_{12}$	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	S II
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4c)	S III
$\mathbf{B}_{14}$	$= -(x_4 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_4 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	S III
$\mathbf{B}_{15}$	$= -x_4 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(4c)	S III
$\mathbf{B}_{16}$	$= (x_4 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_4 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	S III
$\mathbf{B}_{17}$	$= x_5 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(4c)	Ta I
$\mathbf{B}_{18}$	$= -(x_5 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_5 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Ta I
$\mathbf{B}_{19}$	$= -x_5 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(4c)	Ta I

$$\mathbf{B}_{20} = \left(x_5 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right) \mathbf{a}_3 = a \left(x_5 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4} b \hat{\mathbf{y}} - c \left(z_5 - \frac{1}{2}\right) \hat{\mathbf{z}} \quad (4c) \quad \text{Ta I}$$

References

- [1] S. A. Sunshine and J. A. Ibers, *Redetermination of the structures of CuTaS_3 and Nb_2Se_9* , Acta Crystallogr. Sect. C **43**, 1019–1022 (1987), doi:10.1107/S0108270187093168.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.