

CeNi₃ Structure:


AB3_hP24_194_cf_abdk-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/1SSV>

https://aflow.org/prototype-encyclopedia/AB3_hP24_194_cf_abdk-001

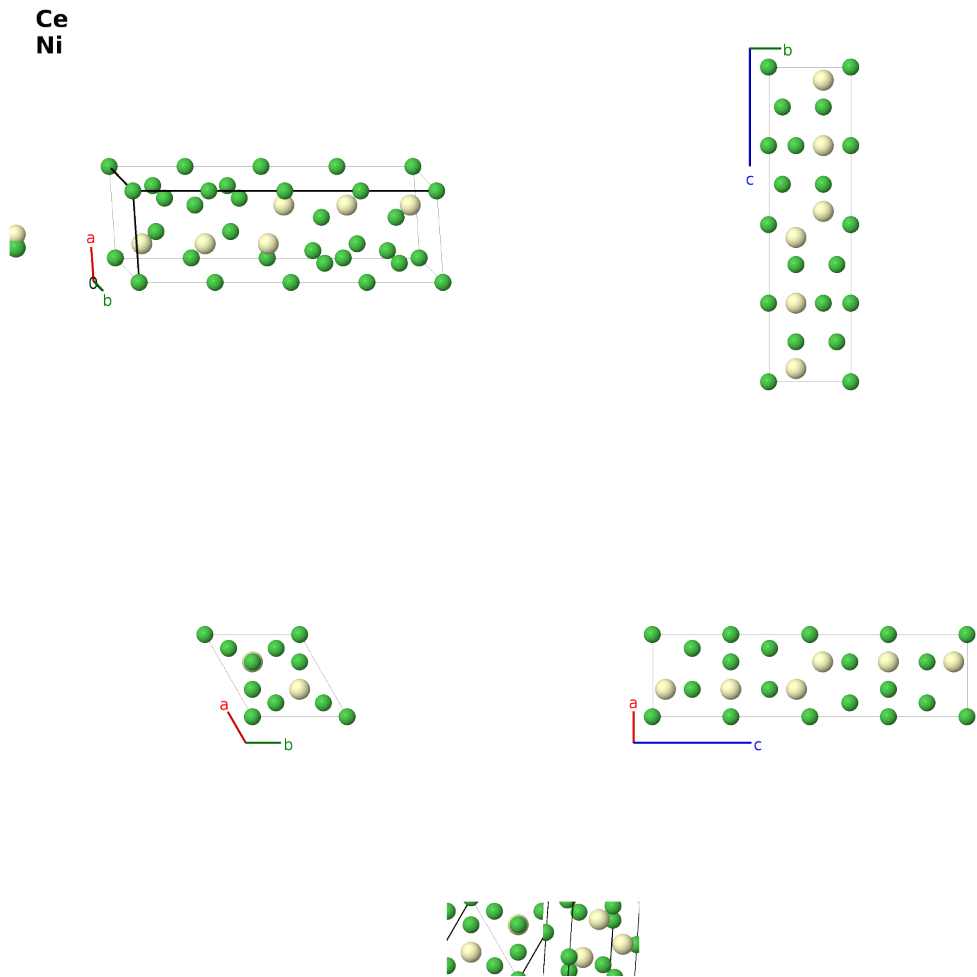


Prototype	CeNi ₃
AFLOW prototype label	AB3_hP24_194_cf_abdk-001
ICSD	102230
CCDC	1660217
Pearson symbol	hP24
Space group number	194
Space group symbol	$P6_3/mmc$

AFLOW prototype command `aflow --proto=AB3_hP24_194_cf_abdk-001`
 `--params= $a, c/a, z_5, x_6, z_6$`

Other compounds with this structure

DyFe₃, GdNi₃, GdRh₃, LaRh₃, LuNi₃, NdNi₃, NdRh₃, SmCo₃, SmRh₃, TbFe₃, YCo₃, YFe₃, YRh₃

Hexagonal primitive vectors

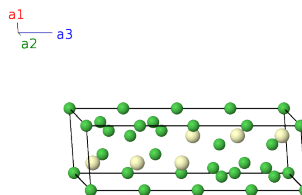

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_3 &= c\hat{\mathbf{z}}\end{aligned}$$

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(2a) Ni I
$\mathbf{B}_2$	$=$	$\frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} c \hat{\mathbf{z}}$	(2a) Ni I
$\mathbf{B}_3$	$=$	$\frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4} c \hat{\mathbf{z}}$	(2b) Ni II
$\mathbf{B}_4$	$=$	$\frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4} c \hat{\mathbf{z}}$	(2b) Ni II
$\mathbf{B}_5$	$=$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + \frac{1}{4} c \hat{\mathbf{z}}$	(2c) Ce I
$\mathbf{B}_6$	$=$	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + \frac{3}{4} c \hat{\mathbf{z}}$	(2c) Ce I
$\mathbf{B}_7$	$=$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + \frac{3}{4} c \hat{\mathbf{z}}$	(2d) Ni III
$\mathbf{B}_8$	$=$	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + \frac{1}{4} c \hat{\mathbf{z}}$	(2d) Ni III
$\mathbf{B}_9$	$=$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(4f) Ce II
$\mathbf{B}_{10}$	$=$	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(4f) Ce II
$\mathbf{B}_{11}$	$=$	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(4f) Ce II
$\mathbf{B}_{12}$	$=$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	(4f) Ce II
$\mathbf{B}_{13}$	$=$	$x_6 \mathbf{a}_1 + 2x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$\frac{3}{2} ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2} ax_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{14}$	$=$	$-2x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$-\frac{3}{2} ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2} ax_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{15}$	$=$	$x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$-\sqrt{3} ax_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{16}$	$=$	$-x_6 \mathbf{a}_1 - 2x_6 \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-\frac{3}{2} ax_6 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2} ax_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{17}$	$=$	$2x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{3}{2} ax_6 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2} ax_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{18}$	$=$	$-x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\sqrt{3} ax_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{19}$	$=$	$2x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$\frac{3}{2} ax_6 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2} ax_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{20}$	$=$	$-x_6 \mathbf{a}_1 - 2x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-\frac{3}{2} ax_6 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2} ax_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{21}$	$=$	$-x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$\sqrt{3} ax_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{22}$	$=$	$-2x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-\frac{3}{2} ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2} ax_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{23}$	$=$	$x_6 \mathbf{a}_1 + 2x_6 \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{3}{2} ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2} ax_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \hat{\mathbf{z}}$	(12k) Ni IV
$\mathbf{B}_{24}$	$=$	$x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-\sqrt{3} ax_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \hat{\mathbf{z}}$	(12k) Ni IV

References

- [1] D. T. Cromer and C. E. Olsen, *The crystal structure of PuNi_3 and CeNi_3* , Acta Cryst. **12**, 689–694 (1959), doi:10.1107/S0365110X59002006.

First cited in

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.