

Bainite (Fe₃C) Structure:

AB3_hP8_182_c_g-001


This structure previously used the label(s) **AB3_hP8_182_c-g**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/JRHU>

https://aflow.org/prototype-encyclopedia/AB3_hP8_182_c_g-001

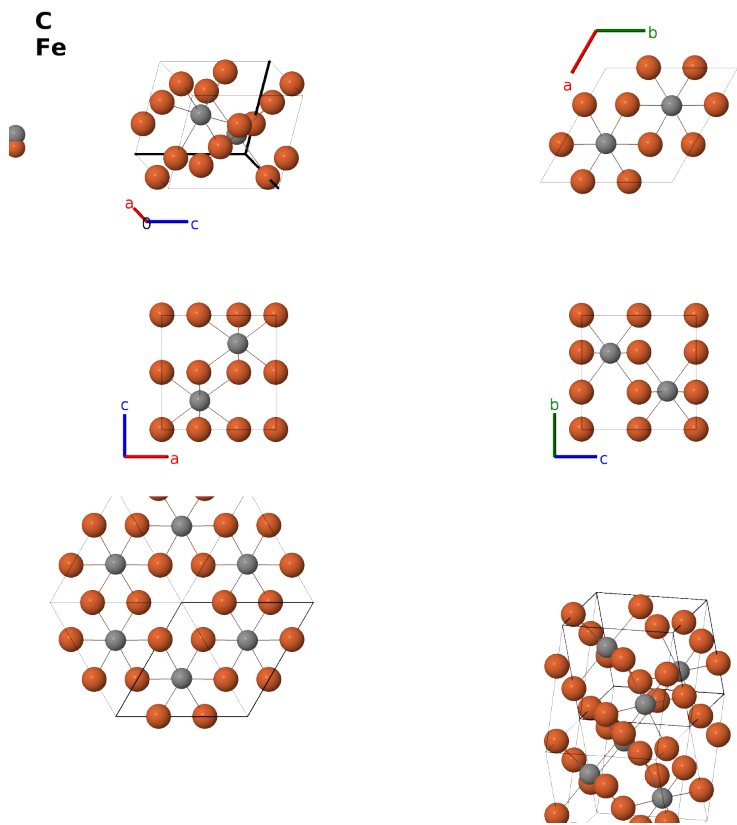

Prototype	Fe ₃ C
AFLOW prototype label	AB3_hP8_182_c_g-001
Mineral name	bainite
Pearson symbol	hP8
Space group number	182
Space group symbol	$P6_322$
AFLOW prototype command	<code>aflow --proto=AB3_hP8_182_c_g-001</code> <code>--params=a, c/a, x₂</code>


Other compounds with this structure

ϵ -Fe₃N

- Strictly speaking, bainite is a microstructure. However, (Villars, 1991) Vol. II, p. 1894, refers to this crystal structure as upper bainite, and (Villars, 2014) refers to this as bainite.

Hexagonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

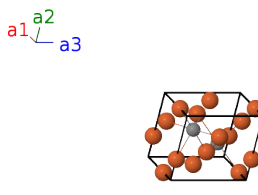

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(2c)	C I
$\mathbf{B}_2$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(2c)	C I
$\mathbf{B}_3$	$= x_2 \mathbf{a}_1$	$=$	$\frac{1}{2}ax_2 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}}$	(6g)	Fe I
$\mathbf{B}_4$	$= x_2 \mathbf{a}_2$	$=$	$\frac{1}{2}ax_2 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}}$	(6g)	Fe I
$\mathbf{B}_5$	$= -x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2$	$=$	$-ax_2 \hat{\mathbf{x}}$	(6g)	Fe I
$\mathbf{B}_6$	$= -x_2 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$-\frac{1}{2}ax_2 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Fe I
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-\frac{1}{2}ax_2 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Fe I
$\mathbf{B}_8$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Fe I

References

- [1] M. Reibold, A. A. Levin, D. C. Meyer, P. Paufler, and W. Kochmann, *Microstructure of a Damascus sabre after annealing*, Int. J. Mater. Res. **97**, 1172–1182 (2006), doi:10.3139/ijmr-2006-0184.
- [2] P. Villars and L. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases* (ASM International, Materials Park, OH, 1991), 2nd edn.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017