

CdPt₃ (“New” *L*₁₃) Structure: AB3_oC8_65_a_bf-001


This structure previously used the label(s) **AB3_oC8_65_a_bf**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/JBK1>

https://aflow.org/prototype-encyclopedia/AB3_oC8_65_a_bf-001

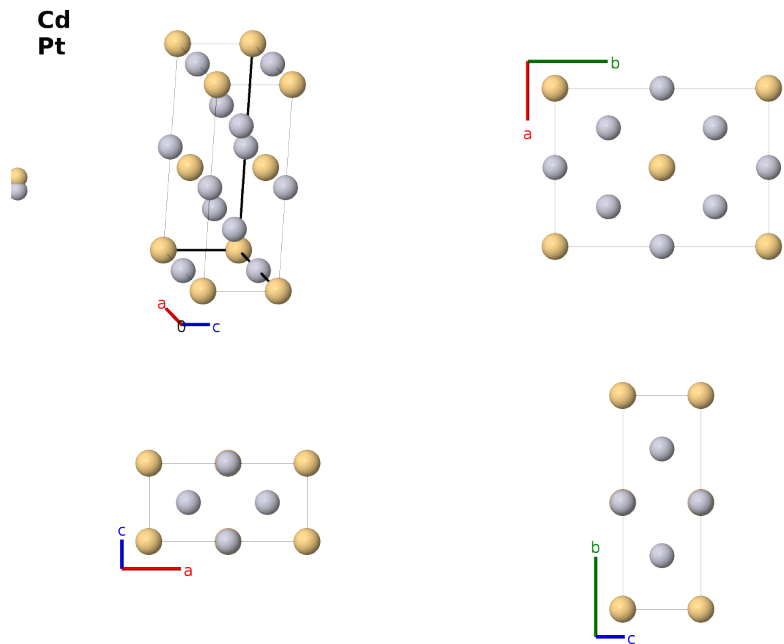


Prototype	CdPt ₃
AFLOW prototype label	AB3_oC8_65_a_bf-001
<i>Strukturbericht</i> designation	<i>L</i> ₁₃
Pearson symbol	oC8
Space group number	65
Space group symbol	<i>Cmmm</i>
AFLOW prototype command	<code>aflow --proto=AB3_oC8_65_a_bf-001</code> <code>--params=a,b/a,c/a</code>

- This is *not* the *L*₁₃ CuPt structure labeled by (Ewald, 1931) as *L*₁₃. That structure is now considered obsolete.
- This structure has not been experimentally confirmed, but it has frequently been predicted as a low energy structure. (Hart, 2009) has a review of these calculations. It was originally given the *L*₁₃ designation. As this has been frequently used in the literature (*e.g.* Mehl, 2017), we will continue to use it despite the possible confusion.

- Data for this structure comes from the supplemental material of (Hart, 2013).

Base-centered Orthorhombic primitive vectors
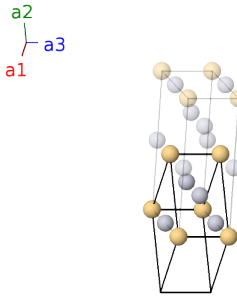
$$\begin{aligned}
 \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\
 \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\
 \mathbf{a}_3 &= c \hat{\mathbf{z}}
 \end{aligned}$$


Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	Cd I
$\mathbf{B}_2$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2}a \hat{\mathbf{x}}$	Pt I
$\mathbf{B}_3$	$=$	$\frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	Pt II
$\mathbf{B}_4$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{4}a \hat{\mathbf{x}} - \frac{1}{4}b \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	Pt II

References

- [1] G. L. W. Hart, *Verifying predictions of the $L1_3$ crystal structure in Cd-Pt and Pd-Pt by exhaustive enumeration*, Phys. Rev. B **80**, 014106 (2009), doi:10.1103/PhysRevB.80.014106.
- [2] G. L. W. Hart, S. Curtarolo, T. B. Massalski, and O. Levy, *Comprehensive Search for New Phases and Compounds in Binary Alloy Systems Based on Platinum-Group Metals, Using a Computational First-Principles Approach*, Phys. Rev. X **3**, 041305 (2013), doi:10.1103/PhysRevX.3.041035.
- [3] P. P. Ewald and C. Hermann, eds., *Strukturbericht 1913-1928* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1931).
- [4] M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW library of crystallographic prototypes: part 1*, Comp. Mater. Sci. **136**, S1–S828 (2017), doi:10.1016/j.commatsci.2017.01.017.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017