

CuTi₃ (*L*6₀) Structure:

AB3_tP4_123_a_ce-001


This structure previously used the label(s) **AB3_tP4_123_a_ce**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/B4JD>

https://aflow.org/prototype-encyclopedia/AB3_tP4_123_a_ce-001

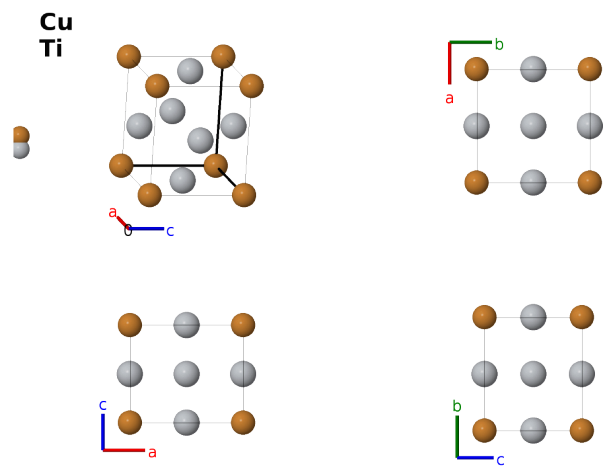

Prototype	CuTi ₃
AFLOW prototype label	AB3_tP4_123_a_ce-001
<i>Strukturbericht</i> designation	<i>L</i> 6 ₀
ICSD	103130
CCDC	1661082
Pearson symbol	tP4
Space group number	123
Space group symbol	<i>P</i> 4/ <i>mmm</i>
AFLOW prototype command	<code>aflow --proto=AB3_tP4_123_a_ce-001</code> <code>--params=a,c/a</code>

Other compounds with this structure

AgZr₃, AlPu₃, BaBi₃, α' CdAu₃, CuZr₃, DyIn₃, GaPu₃, InPt₃, MnAu₃, SrPb₃, TiPd₃

- This is a tetragonal distortion of the *L*1₂ (Cu₃Au) structure. When $c = a$ the atoms are at the positions of a face-centered cubic lattice. If we replace the Ti-I atom by Cu, then the system reduces to the *L*1₀ (CuAu) structure. Interestingly, (Massalski, 1986) lists no stable or metastable structures with composition CuTi₃. (Byström, 1947) do find a phase of CdAu₃ which they say has this structure.


Simple Tetragonal primitive vectors



$$\mathbf{a}_1 = a \hat{\mathbf{x}}$$

$$\mathbf{a}_2 = a \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = c \hat{\mathbf{z}}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(1a) Cu I
$\mathbf{B}_2$	=	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	=	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}}$	(1c) Ti I
$\mathbf{B}_3$	=	$\frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(2e) Ti II
$\mathbf{B}_4$	=	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} c \hat{\mathbf{z}}$	(2e) Ti II

References

- [1] N. Karlsson, *An X-ray study of the phases in the copper–titanium system*, J. Inst. Met. **79**, 391–405 (1951).
- [2] T. B. Massalski, H. Okamoto, P. R. Subramanian, and L. Kacprzak, eds., *Binary Alloy Phase Diagrams* (American Society for Metals, Materials Park, OH, 1990).
- [3] A. Byström and K. E. Almin, *X-ray Investigation of Gold-Cadmium Alloys Rich in Gold*, Acta Chem. Scand. **1**, 76–89 (1947), doi:10.3891/acta.chem.scand.01-0076.

Found in

- [1] P. Villars and K. Cenzual, *Pearson’s Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017