

Room Temperature GaMo₄S₈ Structure: AB4C8_cF52_216_a_e_2e-001


This structure previously used the label(s) **AB4C8_cF52_216_a_e_2e**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/BEEG>

https://aflow.org/prototype-encyclopedia/AB4C8_cF52_216_a_e_2e-001

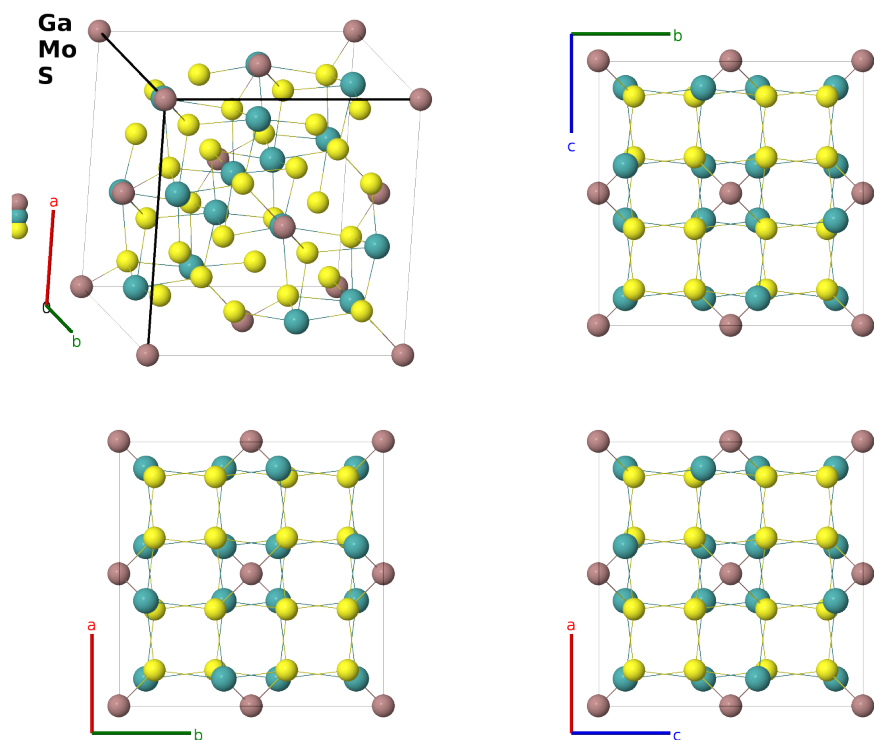

Prototype	GaMo ₄ S ₈
AFLOW prototype label	AB4C8_cF52_216_a_e_2e-001
ICSD	49566
CCDC	1614760
Pearson symbol	cF52
Space group number	216
Space group symbol	$F\bar{4}3m$
AFLOW prototype command	<code>aflow --proto=AB4C8_cF52_216_a_e_2e-001</code> <code>--params=a, x₂, x₃, x₄</code>


Other compounds with this structure

AlMo₄S₈, Co(Mo₂Re₂)S₈, Fe(Mo₂Re₂)S₈, GaMo₄S₄Te₄, GaMo₄S₈, GaMo₄Se₄Te₄, GaMo₄Se₈, GaMo₄Te₈, GaNb₄S₈, GaNb₄Se₈, GaNb₄Te₈, GaRe₄S₈, GaRe₄Se₈, GaRe₄Te₈, GaTa₄S₈, GaTa₄Se₈, GaTa₄Te₈, GaV₄S₈, GaV₄Se₈, GaV₄Te₈, GeMo₄S₈, GeMo₄Se₈, GeMo₄Te₈, GeNb₄S₈, GeNb₄Se₈, GeNb₄Te₈, GeRe₄S₈, GeRe₄Se₈, GeRe₄Te₈, GeTa₄S₈, GeTa₄Se₈, GeTa₄Te₈, GeV₄S₈, GeV₄Se₈, GeV₄Te₈, LaMo₄S₈, Ni(Mo₂Re₂)S₈, Zn(Mo₂Re₂)S₈

- This is the room temperature structure. Below 45K GaMo₄S₈ transforms into a rhombohedral structure.
 - (Ben Yaich, 1984) do not give the lattice constant for GaMo₄S₈. We infer it from their interatomic distances and obtain a value of $a = 9.7294\text{\AA}$. The ICSD entry uses $a = 9.74\text{\AA}$.
-

Face-centered Cubic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}a\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}}\end{aligned}$$

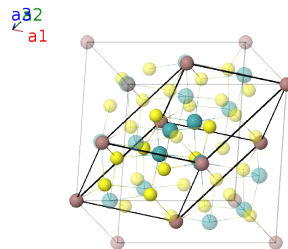

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(4a) Ga I
$\mathbf{B}_2$	=	$x_2\mathbf{a}_1 + x_2\mathbf{a}_2 + x_2\mathbf{a}_3$	=	$ax_2\hat{\mathbf{x}} + ax_2\hat{\mathbf{y}} + ax_2\hat{\mathbf{z}}$	(16e) Mo I
$\mathbf{B}_3$	=	$x_2\mathbf{a}_1 + x_2\mathbf{a}_2 - 3x_2\mathbf{a}_3$	=	$-ax_2\hat{\mathbf{x}} - ax_2\hat{\mathbf{y}} + ax_2\hat{\mathbf{z}}$	(16e) Mo I
$\mathbf{B}_4$	=	$x_2\mathbf{a}_1 - 3x_2\mathbf{a}_2 + x_2\mathbf{a}_3$	=	$-ax_2\hat{\mathbf{x}} + ax_2\hat{\mathbf{y}} - ax_2\hat{\mathbf{z}}$	(16e) Mo I
$\mathbf{B}_5$	=	$-3x_2\mathbf{a}_1 + x_2\mathbf{a}_2 + x_2\mathbf{a}_3$	=	$ax_2\hat{\mathbf{x}} - ax_2\hat{\mathbf{y}} - ax_2\hat{\mathbf{z}}$	(16e) Mo I
$\mathbf{B}_6$	=	$x_3\mathbf{a}_1 + x_3\mathbf{a}_2 + x_3\mathbf{a}_3$	=	$ax_3\hat{\mathbf{x}} + ax_3\hat{\mathbf{y}} + ax_3\hat{\mathbf{z}}$	(16e) S I
$\mathbf{B}_7$	=	$x_3\mathbf{a}_1 + x_3\mathbf{a}_2 - 3x_3\mathbf{a}_3$	=	$-ax_3\hat{\mathbf{x}} - ax_3\hat{\mathbf{y}} + ax_3\hat{\mathbf{z}}$	(16e) S I
$\mathbf{B}_8$	=	$x_3\mathbf{a}_1 - 3x_3\mathbf{a}_2 + x_3\mathbf{a}_3$	=	$-ax_3\hat{\mathbf{x}} + ax_3\hat{\mathbf{y}} - ax_3\hat{\mathbf{z}}$	(16e) S I
$\mathbf{B}_9$	=	$-3x_3\mathbf{a}_1 + x_3\mathbf{a}_2 + x_3\mathbf{a}_3$	=	$ax_3\hat{\mathbf{x}} - ax_3\hat{\mathbf{y}} - ax_3\hat{\mathbf{z}}$	(16e) S I
$\mathbf{B}_{10}$	=	$x_4\mathbf{a}_1 + x_4\mathbf{a}_2 + x_4\mathbf{a}_3$	=	$ax_4\hat{\mathbf{x}} + ax_4\hat{\mathbf{y}} + ax_4\hat{\mathbf{z}}$	(16e) S II
$\mathbf{B}_{11}$	=	$x_4\mathbf{a}_1 + x_4\mathbf{a}_2 - 3x_4\mathbf{a}_3$	=	$-ax_4\hat{\mathbf{x}} - ax_4\hat{\mathbf{y}} + ax_4\hat{\mathbf{z}}$	(16e) S II
$\mathbf{B}_{12}$	=	$x_4\mathbf{a}_1 - 3x_4\mathbf{a}_2 + x_4\mathbf{a}_3$	=	$-ax_4\hat{\mathbf{x}} + ax_4\hat{\mathbf{y}} - ax_4\hat{\mathbf{z}}$	(16e) S II
$\mathbf{B}_{13}$	=	$-3x_4\mathbf{a}_1 + x_4\mathbf{a}_2 + x_4\mathbf{a}_3$	=	$ax_4\hat{\mathbf{x}} - ax_4\hat{\mathbf{y}} - ax_4\hat{\mathbf{z}}$	(16e) S II

References

- [1] H. B. Yaich, J. C. Jegaden, M. P. R. Chevrel, M. Sergent, A. Berton, J. Chaussy, A. K. Rastogi, and R. Tournier, *Nouveaux chalcogenures mixtes GaMo₄(XX)₈ (X = S, Se, Te) à clusters tétraédriques Mo₄*, J. Solid State Chem. **51**, 212–217 (1984), doi:10.1016/0022-4596(84)90336-0.

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.