

Nb₄CoSi Structure:

AB4C_tP12_124_a_m_c-001


This structure previously used the label(s) **AB4C_tP12_124_a_m_c**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/LAN3>

https://aflow.org/prototype-encyclopedia/AB4C_tP12_124_a_m_c-001

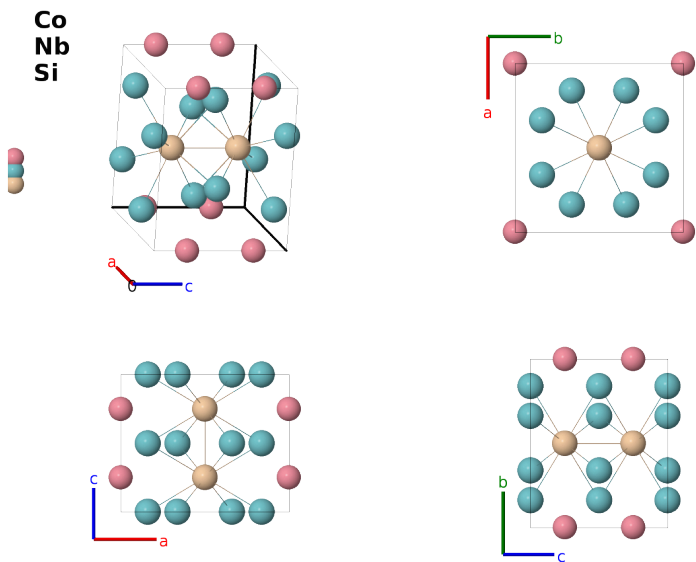


Prototype	CoNb ₄ Si
AFLOW prototype label	AB4C_tP12_124_a_m_c-001
ICSD	43233
CCDC	1612756
Pearson symbol	tP12
Space group number	124
Space group symbol	<i>P4/mcc</i>
AFLOW prototype command	<code>aflow --proto=AB4C_tP12_124_a_m_c-001</code> <code>--params=<i>a, c/a, x₃, y₃</i></code>

Other compounds with this structure

Nb₄FeSi, Nb₄NiSi

Simple Tetragonal primitive vectors

$\mathbf{a}_1$ $\mathbf{a}_2$
 $\mathbf{a}_3$



$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4} c \hat{\mathbf{z}}$	(2a)	Co I
$\mathbf{B}_2$	$= \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4} c \hat{\mathbf{z}}$	(2a)	Co I
$\mathbf{B}_3$	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{4} c \hat{\mathbf{z}}$	(2c)	Si I
$\mathbf{B}_4$	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{3}{4} c \hat{\mathbf{z}}$	(2c)	Si I
$\mathbf{B}_5$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2$	$=$	$ax_3 \hat{\mathbf{x}} + ay_3 \hat{\mathbf{y}}$	(8m)	Nb I
$\mathbf{B}_6$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2$	$=$	$-ax_3 \hat{\mathbf{x}} - ay_3 \hat{\mathbf{y}}$	(8m)	Nb I
$\mathbf{B}_7$	$= -y_3 \mathbf{a}_1 + x_3 \mathbf{a}_2$	$=$	$-ay_3 \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}}$	(8m)	Nb I
$\mathbf{B}_8$	$= y_3 \mathbf{a}_1 - x_3 \mathbf{a}_2$	$=$	$ay_3 \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}}$	(8m)	Nb I
$\mathbf{B}_9$	$= -x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + ay_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(8m)	Nb I
$\mathbf{B}_{10}$	$= x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} - ay_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(8m)	Nb I
$\mathbf{B}_{11}$	$= y_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ay_3 \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(8m)	Nb I
$\mathbf{B}_{12}$	$= -y_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ay_3 \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(8m)	Nb I

References

- [1] E. I. Gladyshevskii and Y. B. Kuz'ma, *The compounds Nb_4FeSi , Nb_4CoSi , Nb_4NiSi and their crystal structures*, J. Struct. Chem. **6** (1965), doi:10.1007/BF00743870.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043