

Ta₂PdSe₆ Structure: AB6C2_mC18_12_a_3i_i-004


This structure previously used the label(s) **AB6C2_mC18_12.a_3i.i**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/H8PR>

https://aflow.org/prototype-encyclopedia/AB6C2_mC18_12.a_3i_i-004

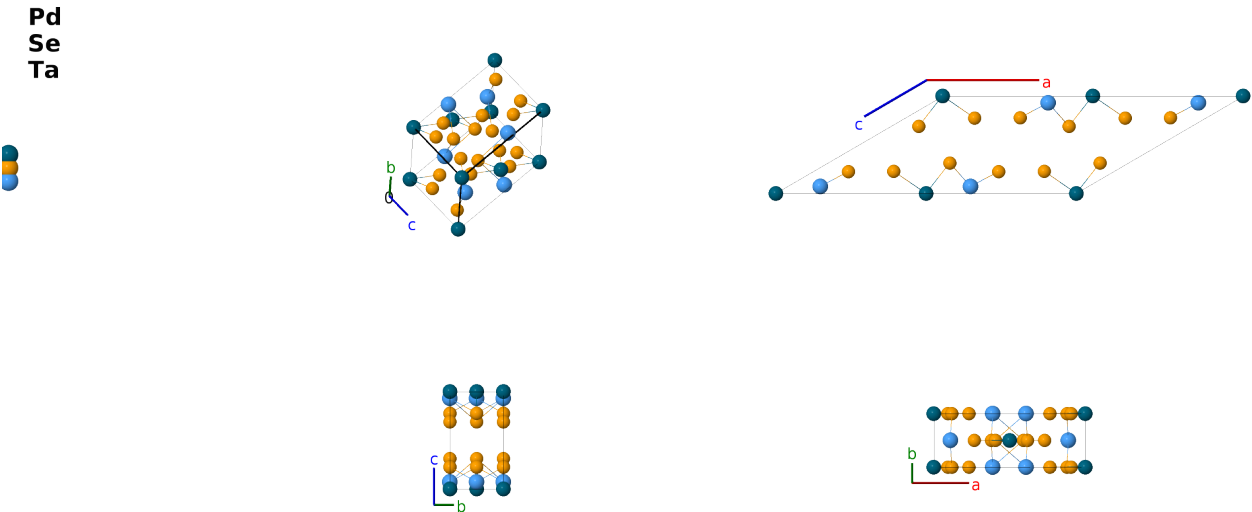

Prototype	PdSe ₆ Ta ₂
AFLOW prototype label	AB6C2_mC18_12.a_3i_i-004
ICSD	61005
CCDC	1624559
Pearson symbol	mC18
Space group number	12
Space group symbol	$C2/m$
AFLOW prototype command	<code>aflow --proto=AB6C2_mC18_12.a_3i_i-004</code> <code>--params=a,b/a,c/a,β,x_2,z_2,x_3,z_3,x_4,z_4,x_5,z_5</code>


Other compounds with this structure

Nb₂PdS₆, Nb₂PdSe₆, Ta₂PdS₆

- (Keszler, 1985) gave the structure in the $I2/m$ setting of space group #12. We used FINDSYM to change this to the standard $C2/m$ setting. Because of this change our primitive vectors are linear combinations of the original ones, and the lattice has been rotated.

Base-centered Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(2a) Pd I
$\mathbf{B}_2$	$=$	$x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4i) Se I
$\mathbf{B}_3$	$=$	$-x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4i) Se I
$\mathbf{B}_4$	$=$	$x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4i) Se II
$\mathbf{B}_5$	$=$	$-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4i) Se II
$\mathbf{B}_6$	$=$	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4i) Se III
$\mathbf{B}_7$	$=$	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4i) Se III
$\mathbf{B}_8$	$=$	$x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4i) Ta I
$\mathbf{B}_9$	$=$	$-x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4i) Ta I

References

- [1] D. A. Keszler, P. J. Squattrito, N. E. Brese, J. A. Ibers, M. Shang, and J. Lu, *New layered ternary chalcogenides: tantalum palladium sulfide (Ta_2PdS_6), tantalum palladium selenide (Ta_2PdSe_6), niobium palladium sulfide (Nb_2PdS_6), niobium palladium selenide (Nb_2PdSe_6)*, Inorg. Chem. pp. 3063–3067 (1985), doi:10.1021/ic00213a038.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.