

Ta₆S Structure:


AB6_mC56_15_f_6f-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/HXME>

https://aflow.org/prototype-encyclopedia/AB6_mC56_15_f_6f-001

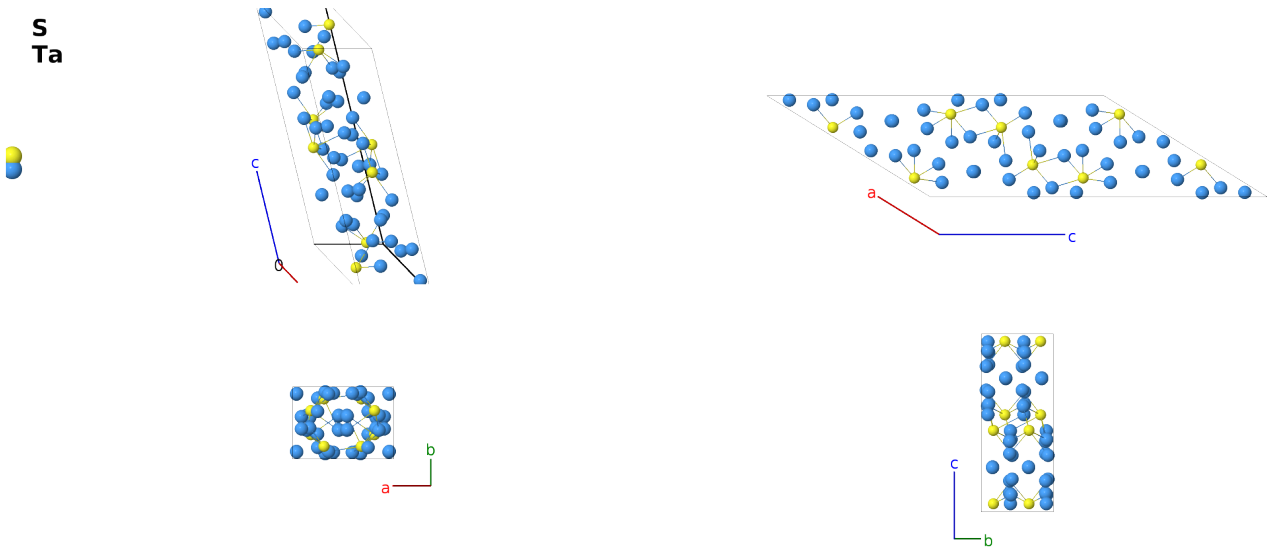

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= (x_1 - y_1) \mathbf{a}_1 + (x_1 + y_1) \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(8f)	S I
$\mathbf{B}_2$	$= -(x_1 + y_1) \mathbf{a}_1 - (x_1 - y_1) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	S I
$\mathbf{B}_3$	$= -(x_1 - y_1) \mathbf{a}_1 - (x_1 + y_1) \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(8f)	S I
$\mathbf{B}_4$	$= (x_1 + y_1) \mathbf{a}_1 + (x_1 - y_1) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	S I
$\mathbf{B}_5$	$= (x_2 - y_2) \mathbf{a}_1 + (x_2 + y_2) \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta I
$\mathbf{B}_6$	$= -(x_2 + y_2) \mathbf{a}_1 - (x_2 - y_2) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ta I
$\mathbf{B}_7$	$= -(x_2 - y_2) \mathbf{a}_1 - (x_2 + y_2) \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta I
$\mathbf{B}_8$	$= (x_2 + y_2) \mathbf{a}_1 + (x_2 - y_2) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ta I
$\mathbf{B}_9$	$= (x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta II
$\mathbf{B}_{10}$	$= -(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ta II
$\mathbf{B}_{11}$	$= -(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta II
$\mathbf{B}_{12}$	$= (x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ta II
$\mathbf{B}_{13}$	$= (x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta III
$\mathbf{B}_{14}$	$= -(x_4 + y_4) \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ta III
$\mathbf{B}_{15}$	$= -(x_4 - y_4) \mathbf{a}_1 - (x_4 + y_4) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta III
$\mathbf{B}_{16}$	$= (x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ta III
$\mathbf{B}_{17}$	$= (x_5 - y_5) \mathbf{a}_1 + (x_5 + y_5) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta IV
$\mathbf{B}_{18}$	$= -(x_5 + y_5) \mathbf{a}_1 - (x_5 - y_5) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ta IV
$\mathbf{B}_{19}$	$= -(x_5 - y_5) \mathbf{a}_1 - (x_5 + y_5) \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta IV
$\mathbf{B}_{20}$	$= (x_5 + y_5) \mathbf{a}_1 + (x_5 - y_5) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Ta IV
$\mathbf{B}_{21}$	$= (x_6 - y_6) \mathbf{a}_1 + (x_6 + y_6) \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(8f)	Ta V

$$\begin{aligned}
\mathbf{B}_{22} &= \begin{matrix} -(x_6 + y_6) \mathbf{a}_1 - (x_6 - y_6) \mathbf{a}_2 - \\ (z_6 - \frac{1}{2}) \mathbf{a}_3 \end{matrix} = \begin{matrix} -(ax_6 + c(z_6 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} - \\ c(z_6 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{matrix} & (8f) & \text{Ta V} \\
\mathbf{B}_{23} &= \begin{matrix} -(x_6 - y_6) \mathbf{a}_1 - (x_6 + y_6) \mathbf{a}_2 - \\ z_6 \mathbf{a}_3 \end{matrix} = \begin{matrix} -(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}} \end{matrix} & (8f) & \text{Ta V} \\
\mathbf{B}_{24} &= \begin{matrix} (x_6 + y_6) \mathbf{a}_1 + (x_6 - y_6) \mathbf{a}_2 + \\ (z_6 + \frac{1}{2}) \mathbf{a}_3 \end{matrix} = \begin{matrix} (ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + \\ c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{matrix} & (8f) & \text{Ta V} \\
\mathbf{B}_{25} &= \begin{matrix} (x_7 - y_7) \mathbf{a}_1 + (x_7 + y_7) \mathbf{a}_2 + \\ z_7 \mathbf{a}_3 \end{matrix} = \begin{matrix} (ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}} \end{matrix} & (8f) & \text{Ta VI} \\
\mathbf{B}_{26} &= \begin{matrix} -(x_7 + y_7) \mathbf{a}_1 - (x_7 - y_7) \mathbf{a}_2 - \\ (z_7 - \frac{1}{2}) \mathbf{a}_3 \end{matrix} = \begin{matrix} -(ax_7 + c(z_7 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} - \\ c(z_7 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{matrix} & (8f) & \text{Ta VI} \\
\mathbf{B}_{27} &= \begin{matrix} -(x_7 - y_7) \mathbf{a}_1 - (x_7 + y_7) \mathbf{a}_2 - \\ z_7 \mathbf{a}_3 \end{matrix} = \begin{matrix} -(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}} \end{matrix} & (8f) & \text{Ta VI} \\
\mathbf{B}_{28} &= \begin{matrix} (x_7 + y_7) \mathbf{a}_1 + (x_7 - y_7) \mathbf{a}_2 + \\ (z_7 + \frac{1}{2}) \mathbf{a}_3 \end{matrix} = \begin{matrix} (ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + \\ c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{matrix} & (8f) & \text{Ta VI}
\end{aligned}$$

References

- [1] H. F. Franzen and J. G. Smeggil, *The Crystal Structure of Ta₆S*, Acta Crystallogr. Sect. B **26**, 125–129 (1970), doi:10.1107/S0567740870002054.

Found in

- [1] H. F. Franzen, *Structure and bonding in metal-rich compounds: Pnictides, chalcides and halides*, Prog. Solid St. Chem. **12**, 1–39 (1978), doi:10.1016/0079-6786(78)90002-X.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.