

Zlatogorite (CuNiSb₂) Structure: ABC2_hP4_164_a_b_d-001


This structure previously used the label(s) `ABC2_hP4_164_a_b_d`. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/PUFU>

https://aflow.org/prototype-encyclopedia/ABC2_hP4_164_a_b_d-001

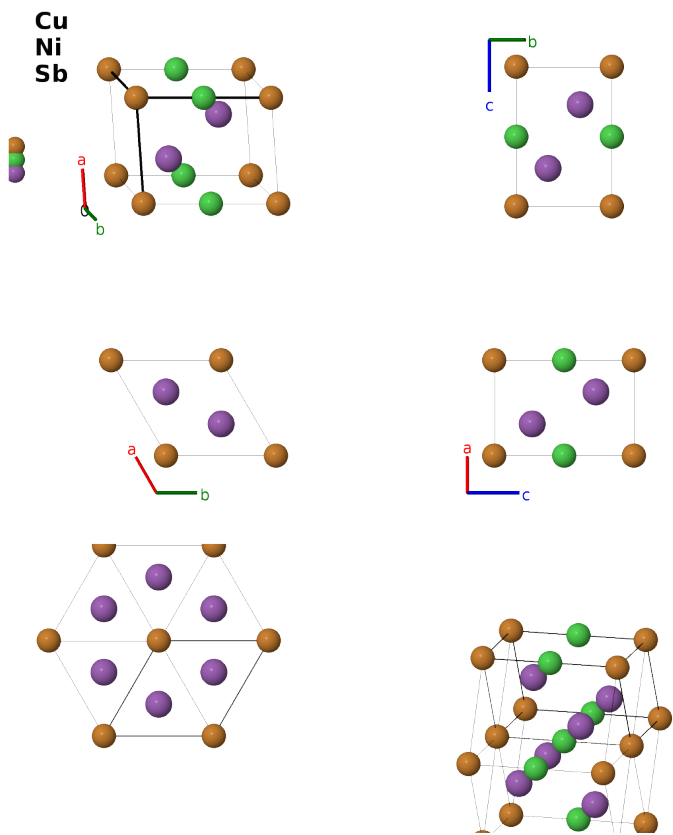


Prototype	CuNiSb ₂
AFLOW prototype label	ABC2_hP4_164_a_b_d-001
Mineral name	zlatogorite
ICSD	134019
CCDC	2010628
Pearson symbol	hP4
Space group number	164
Space group symbol	$P\bar{3}m1$

AFLOW prototype command `aflow --proto=ABC2_hP4_164_a_b_d-001`
 `--params=a, c/a, z3`

- Although we use the data from (Kift, 2010), the ICSD entry is from (Skaggs, 2020).

Trigonal (Hexagonal) primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_3 &= c\hat{\mathbf{z}}\end{aligned}$$

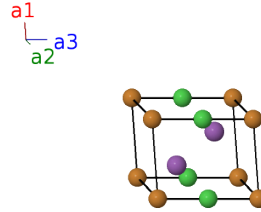

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	Cu I
$\mathbf{B}_2$	$=$	$\frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{2}c\hat{\mathbf{z}}$	Ni I
$\mathbf{B}_3$	$=$	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_3\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_3\hat{\mathbf{z}}$	Sb I
$\mathbf{B}_4$	$=$	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 - z_3\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} - cz_3\hat{\mathbf{z}}$	Sb I

References

- [1] R. L. Kift, *Intermetallic Compounds by Reductive Annealing*, Ph.D. thesis, University of Hull (2010).
- [2] C. M. Skaggs, C.-J. Kang, C. J. Perez, J. Hadermann, T. J. Emge, C. E. Frank, C. Pak, S. H. Lapidus, D. Walker, G. Kotliar, S. M. Kauzlarich, X. Tan, and M. Greenblatt, *Ambient and High Pressure CuNiSb₂: Metal-Ordered and Metal-Disordered NiAs-Type Derivative Pnictides*, Inorg. Chem. **59**, 14058–14069 (2020), doi:10.1021/acs.inorgchem.0c01848.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043