

O2-LiCoO₂ Structure:


ABC2_hP8_186_b_b_ab-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/5BYD>

https://aflow.org/prototype-encyclopedia/ABC2_hP8_186_b_b_ab-001

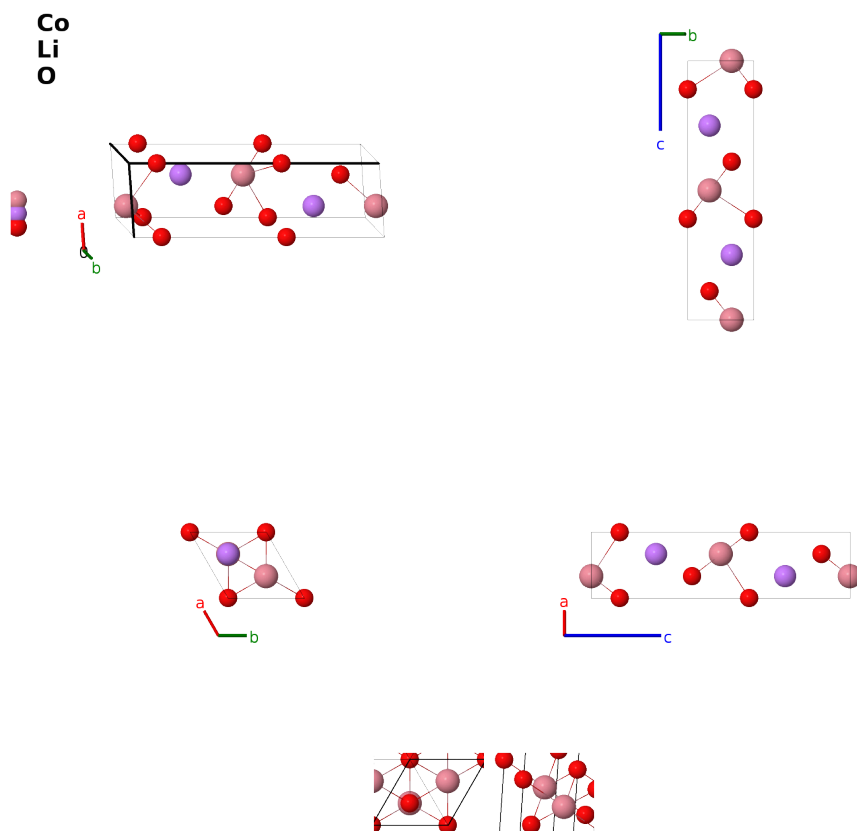


Prototype	CoLiO ₂
AFLOW prototype label	ABC2_hP8_186_b_b_ab-001
Pearson symbol	hP8
Space group number	186
Space group symbol	$P6_3mc$
AFLOW prototype command	<code>aflow --proto=ABC2_hP8_186_b_b_ab-001 --params=a, c/a, z₁, z₂, z₃, z₄</code>

- LiCoO₂ structures are defined by the stacking arrangement of the edge-shared CoO₆ octahedra. In addition, the O3 and O4 structures may have stacking faults. (Yabuuchi, 2013) prepared all of these structures by treating “OP4”-LiNaCo₂O₄ using ion-exchange in aqueous media.

- In O2-LiCoO₂ (this structure) the octahedra are stacked in an alternating cubic/hexagonal arrangement.
- In O3-LiCoO₃ the octahedra are stacked in a cubic arrangement, taking on the α -NaFeO₂ structure.
- In O4-LiCoO₂ the octahedra alternate between O2 and O4.
- (Delmas, 1982) give the composition of this sample as Li_{0.93}CoO_{1.96}. They state that the system is in space group $P3m1$ #156, but the coordinates they give imply that all of the lithium and cobalt atoms are in equivalent positions, and the space group becomes $P6_3mc$ #186.
- Space group $P6_3mc$ #186 does not specify the origin of the z -coordinate. We fix it here by setting $z_2 = 0$.

Hexagonal primitive vectors
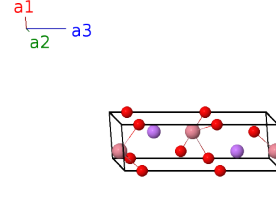
$$\begin{aligned}
 \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\
 \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\
 \mathbf{a}_3 &= c \hat{\mathbf{z}}
 \end{aligned}$$


Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= z_1 \mathbf{a}_3$	$=$	$c z_1 \hat{\mathbf{z}}$	(2a)	O I
$\mathbf{B}_2$	$= (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$c (z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(2a)	O I
$\mathbf{B}_3$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c z_2 \hat{\mathbf{z}}$	(2b)	Co I
$\mathbf{B}_4$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c (z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Co I
$\mathbf{B}_5$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c z_3 \hat{\mathbf{z}}$	(2b)	Li I
$\mathbf{B}_6$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c (z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	Li I
$\mathbf{B}_7$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c z_4 \hat{\mathbf{z}}$	(2b)	O II
$\mathbf{B}_8$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c (z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	O II

References

- [1] C. Delmas, J.-J. Braconnier, and P. Hagenmuller, *A new variety of LiCoO₂ with an unusual oxygen packing obtained by exchange reaction*, Mater. Res. Bull. **17**, 117–123 (1982), doi:10.1016/0025-5408(82)90192-1.

Found in

- [1] N. Yabuuchi, Y. Kawamoto, R. Hara, T. Ishigaki, A. Hoshikawa, M. Yonemura, T. Kamiyama, and S. Komaba, *A Comparative Study of LiCoO₂ Polymorphs: Structural and Electrochemical Characterization of O2-, O3-, and O4-type Phases*, Inorg. Chem. **52**, 9131–9142 (2013), doi:10.1021/ic4013922.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.