

KFeS₂ (*F*5_a) Structure: ABC2_mC16_15_e_e_f-004


This structure previously used the label(s) `ABC2_mC16_15_e_e_f`. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/G8C6>

https://aflow.org/prototype-encyclopedia/ABC2_mC16_15_e_e_f-004

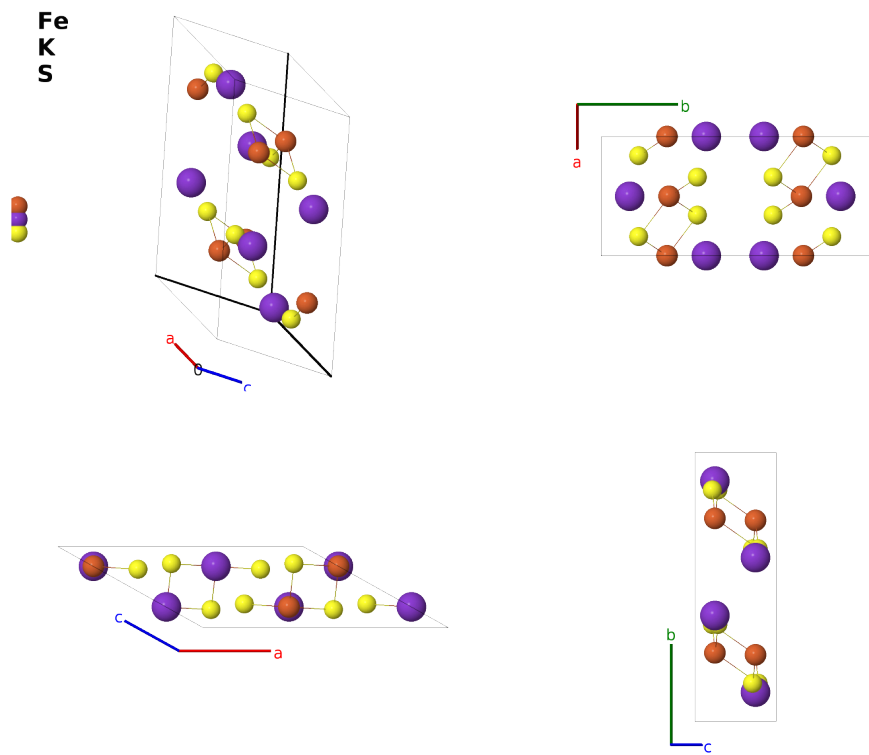

Prototype	FeKS ₂
AFLOW prototype label	ABC2_mC16_15_e_e_f-004
<i>Strukturbericht</i> designation	<i>F</i> 5 _a
ICSD	202380
CCDC	1706962
Pearson symbol	mC16
Space group number	15
Space group symbol	<i>C</i> 2/ <i>c</i>
AFLOW prototype command	<code>aflow --proto=ABC2_mC16_15_e_e_f-004</code> <code>--params=<i>a</i>, <i>b</i>/<i>a</i>, <i>c</i>/<i>a</i>, β, <i>y</i>₁, <i>y</i>₂, <i>x</i>₃, <i>y</i>₃, <i>z</i>₃</code>


Other compounds with this structure

RbFeS₂, KFeSe₂, RbFeSe₂, CsGaS₂, CsGaSe₂

- This structure forms cages of Fe atoms surrounded by tetrahedra of S atoms.

Base-centered Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$

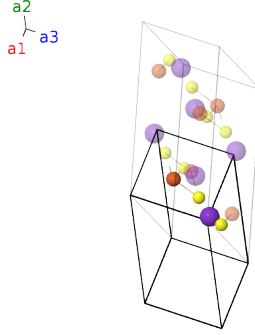

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Fe I
$\mathbf{B}_2$	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Fe I
$\mathbf{B}_3$	$= -y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	K I
$\mathbf{B}_4$	$= y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	K I
$\mathbf{B}_5$	$= (x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	S I
$\mathbf{B}_6$	$= -(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	S I
$\mathbf{B}_7$	$= -(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	S I
$\mathbf{B}_8$	$= (x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	S I

References

- [1] W. Bronger, A. Kyas, and P. Müller, *The antiferromagnetic structures of KFeS₂, RbFeS₂, KFeSe₂, and RbFeSe₂ and the correlation between magnetic moments and crystal field calculations*, J. Solid State Chem. **70**, 262–270 (1987), doi:10.1016/0022-4596(87)90065-X.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.