


Predicted ζ -LiAlO₂ Structure: ABC2_mC24_12_ah_cg_ij-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/JWKX>

https://aflow.org/prototype-encyclopedia/ABC2_mC24_12_ah_cg_ij-001

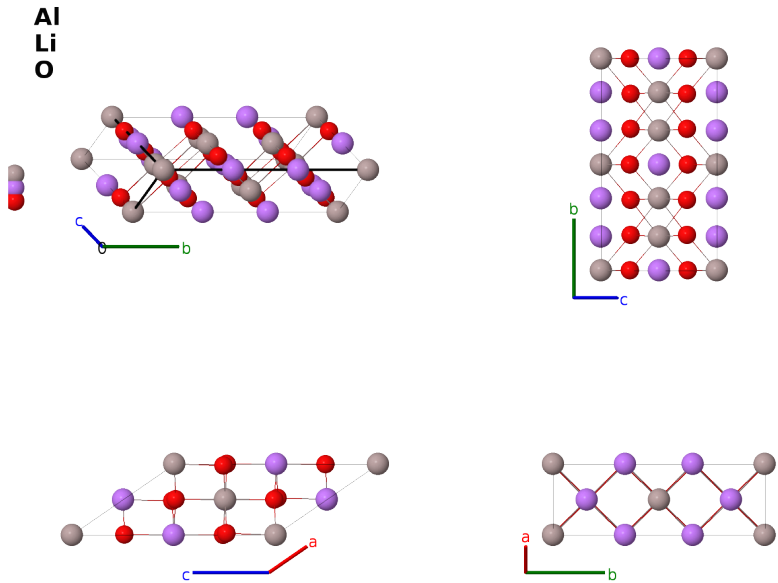

Prototype	AlLiO ₂
AFLOW prototype label	ABC2_mC24_12_ah_cg_ij-001
Pearson symbol	mC24
Space group number	12
Space group symbol	$C2/m$
AFLOW prototype command	<code>aflow --proto=ABC2_mC24_12_ah_cg_ij-001 --params=a, b/a, c/a, β, y_3, y_4, x_5, z_5, x_6, y_6, z_6</code>


- LiAlO₂ exists in many different forms. We describe them using the notation of (Liu, 2018):
 - α , synthesized from Al₂O₃ and Li₂CO₃ at 600°C (Marezio, 1966) forms in the Caswellsilverite $F5_1$ structure, space group $R\bar{3}m$ #166.
 - β is the low temperature structure (Thery, 1961) forming in the LiGaO₂ structure, space group $Pna2_1$ #33.
 - β' is a high-pressure monoclinic phase formed at 1.8 GPa and 370°C, but there is not enough information provided to determine either the space group or occupied Wyckoff positions (Chang, 1968).

- γ is the standard phase under ambient conditions. It is tetragonal (Marezio, 1965), space group $P4_12_12$ #92.
- δ is formed at high pressures (9 GPa) under shock compression and takes the γ -LiFeO₂ structure.
- ϵ , formed from Al₂O₃ and LiH at 500°C, (Debray, 1960) is a cubic phase (space group $I4_132$ #214) with 48 formula units in a cube 12.65Å on a side, but the atomic positions were not determined.
- ζ (this structure) is a predicted high-pressure monoclinic structure (Liu, 2018), (space group $C2/m$ #12). It is apparently not related to the β' phase.

- The α , β' and δ phases are metastable under ambient conditions, but transform to γ -LiAlO₂ upon heating. (Liu, 2008)
- Data for ζ -LiAlO₂ was taken from the calculations of (Liu, 2018) at 40 GPa.

Base-centered Monoclinic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}} \end{aligned}$$

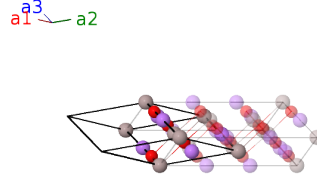

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	0	$=$	0	(2a)	Al I
$\mathbf{B}_2$	$\frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}c \cos \beta \hat{\mathbf{x}} + \frac{1}{2}c \sin \beta \hat{\mathbf{z}}$	(2c)	Li I
$\mathbf{B}_3$	$-y_3 \mathbf{a}_1 + y_3 \mathbf{a}_2$	$=$	$by_3 \hat{\mathbf{y}}$	(4g)	Li II
$\mathbf{B}_4$	$y_3 \mathbf{a}_1 - y_3 \mathbf{a}_2$	$=$	$-by_3 \hat{\mathbf{y}}$	(4g)	Li II
$\mathbf{B}_5$	$-y_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}c \cos \beta \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + \frac{1}{2}c \sin \beta \hat{\mathbf{z}}$	(4h)	Al II
$\mathbf{B}_6$	$y_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}c \cos \beta \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + \frac{1}{2}c \sin \beta \hat{\mathbf{z}}$	(4h)	Al II
$\mathbf{B}_7$	$x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4i)	O I
$\mathbf{B}_8$	$-x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4i)	O I
$\mathbf{B}_9$	$(x_6 - y_6) \mathbf{a}_1 + (x_6 + y_6) \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(8j)	O II
$\mathbf{B}_{10}$	$-(x_6 + y_6) \mathbf{a}_1 - (x_6 - y_6) \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(8j)	O II
$\mathbf{B}_{11}$	$-(x_6 - y_6) \mathbf{a}_1 - (x_6 + y_6) \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(8j)	O II
$\mathbf{B}_{12}$	$(x_6 + y_6) \mathbf{a}_1 + (x_6 - y_6) \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(8j)	O II

References

- [1] G. Liu and H. Liu, *First principles study of LiAlO₂: new dense monoclinic phase under high pressure*, J. Phys.: Condens. Matter **30**, 115401 (2018), doi:10.1088/1361-648X/aaad23.
- [2] L. Lei, D. He, Y. Zou, W. Zhang, Z. Wang, M. Jiang, and M. Du, *J. Solid State Chem.*, Phase transitions of LiAlO₂ at high pressure and high temperature **181**, 1810–1815 (2008), doi:10.1016/j.jssc.2008.04.006.

- [3] M. Marezio, *The crystal structure and anomalous dispersion of γ -LiAlO₂*, Acta Cryst. **19**, 396–400 (1965), doi:10.1107/S0365110X65003511.
- [4] J. Théry, A.-M. Lejus, D. Briançon, and R. Collongues, *Sur la structure et les propriétés des aluminates alcalins*, Bull. Soc. chim. Fr. pp. 973–975 (1961).
- [5] L. Debray and A. Hardy, *Contribution à l'étude structurale des aluminates de lithium*, C. R. Hebd. Séances Acad. Sci. **251**, 725–726 (1960).

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.