

HoCuP₂ Structure:

ABC2_oC16_67_a_g_bg-001


This structure previously used the label(s) **ABC2_oC16_67.b_g.ag**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/BX6K>


https://aflow.org/prototype-encyclopedia/ABC2_oC16_67_a_g_bg-001

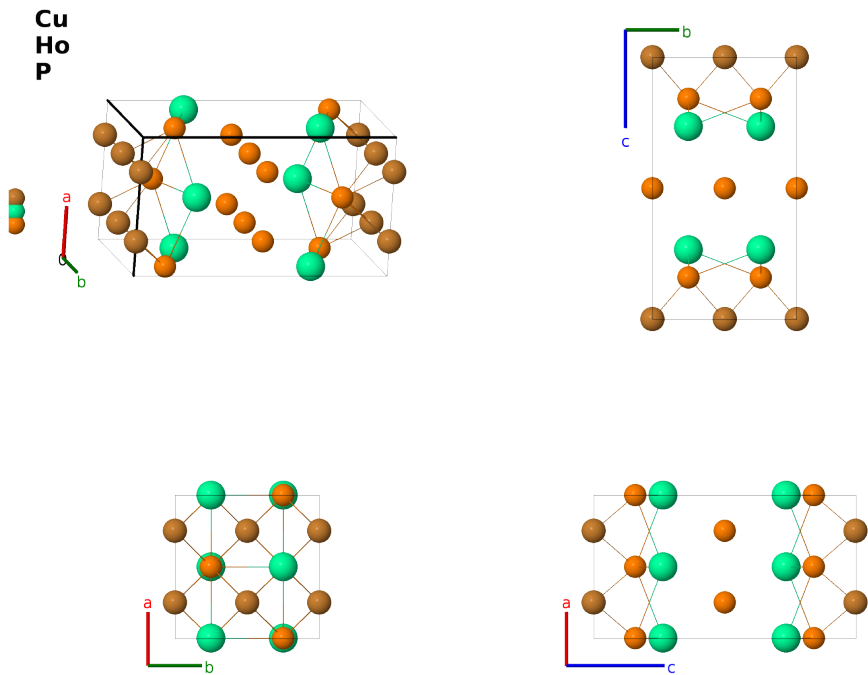

Prototype	CuHoP ₂
AFLOW prototype label	ABC2_oC16_67_a_g_bg-001
ICSD	94443
CCDC	1653878
Pearson symbol	oC16
Space group number	67
Space group symbol	<i>Cmme</i>
AFLOW prototype command	<code>aflow --proto=ABC2_oC16_67_a_g_bg-001</code> <code>--params=a, b/a, c/a, z₃, z₄</code>

- Al_2CuIr (A2BC_oC16_67_ag_b.g) and CuHoP_2 (ABC2_oC16_67_b_g_ag) have similar AFLOW prototype labels (i.e., same symmetry and set of Wyckoff positions with different stoichiometry labels due to alphabetic ordering of atomic species). They are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Base-centered Orthorhombic primitive vectors
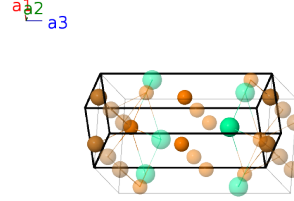
$$\begin{aligned}
 \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\
 \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\
 \mathbf{a}_3 &= c \hat{\mathbf{z}}
 \end{aligned}$$


Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2$	$=$	$\frac{1}{4}a \hat{\mathbf{x}}$	(4a)	Cu I
$\mathbf{B}_2$	$= \frac{3}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2$	$=$	$\frac{3}{4}a \hat{\mathbf{x}}$	(4a)	Cu I
$\mathbf{B}_3$	$= \frac{1}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4b)	P I
$\mathbf{B}_4$	$= \frac{3}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{3}{4}a \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4b)	P I
$\mathbf{B}_5$	$= \frac{3}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{4}b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4g)	Ho I
$\mathbf{B}_6$	$= \frac{1}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4g)	Ho I
$\mathbf{B}_7$	$= \frac{3}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{4}b \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4g)	P II
$\mathbf{B}_8$	$= \frac{1}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(4g)	P II

References

- [1] Y. Mozharivsky, D. Kaczorowski, and H. F. Franzen, *Symmetry-Breaking Transitions in $\text{HoCuAs}_{2-x}\text{P}_x$ and $\text{ErCuAs}_{2-x}\text{P}_x$ ($x=0-2$): Crystal Structure, Application of Landau Theory, Magnetic and Electrical Properties*, Z. Anorganische und Allgemeine Chemie **627**, 2163–2172 (2001), doi:10.1002/1521-3749(200109)627:9<2163::AID-ZAAC2163>3.0.CO;2-N.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043