

LiGaO₂ Structure:

ABC2_oP16_33_a_a_2a-003


This structure previously used the label(s) **ABC2_oP16_33_a_a_2a**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/9S7L>

https://aflow.org/prototype-encyclopedia/ABC2_oP16_33_a_a_2a-003

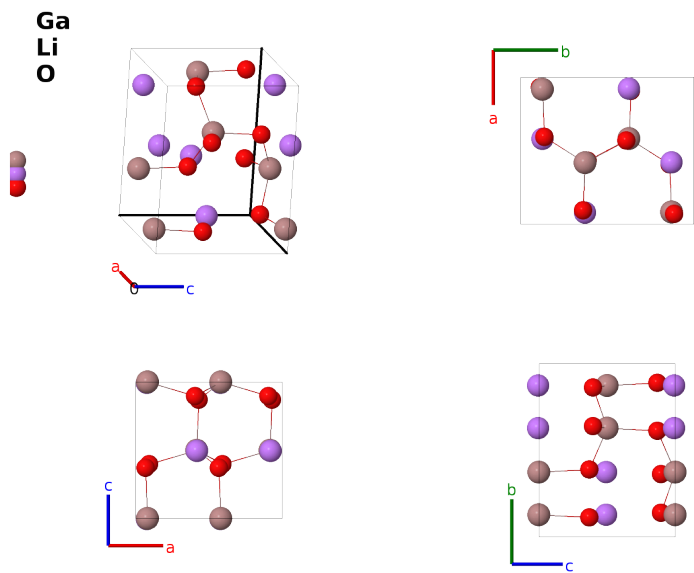

Prototype	GaLiO ₂
AFLOW prototype label	ABC2_oP16_33_a_a_2a-003
ICSD	18152
CCDC	1597708
Pearson symbol	oP16
Space group number	33
Space group symbol	<i>Pna</i> 2 ₁
AFLOW prototype command	<code>aflow --proto=ABC2_oP16_33_a_a_2a-003</code> <code>--params=<i>a, b/a, c/a, x₁, y₁, z₁, x₂, y₂, z₂, x₃, y₃, z₃, x₄, y₄, z₄</i></code>

Other compounds with this structure

BeNSi₂, LiAgN₂, LiAlSe₂, LiGaSe₂, LiVN₂, MgSiN₂, MnGeN₂, NaFeO₂, NaGaO₂, ZnGeN₂


- Space group *Pna*2₁ #33 is polar and so allows an arbitrary choice of the zero of the *z*-axis. Here we set *z*₁ = 0 for gallium.

- β -NaFeO₂ and LiGaO₂ have the same AFLOW prototype label, ABC2_oP16_33_a_a_2a. They are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

$\mathbf{a}_1$ $\mathbf{a}_2$
 $\mathbf{a}_3$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4a)	Ga I
$\mathbf{B}_2$	$= -x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Ga I
$\mathbf{B}_3$	$= (x_1 + \frac{1}{2}) \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4a)	Ga I
$\mathbf{B}_4$	$= -(x_1 - \frac{1}{2}) \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Ga I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4a)	Li I
$\mathbf{B}_6$	$= -x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Li I
$\mathbf{B}_7$	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4a)	Li I
$\mathbf{B}_8$	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Li I
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_{10}$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_{11}$	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_{12}$	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4a)	O II
$\mathbf{B}_{14}$	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	O II
$\mathbf{B}_{15}$	$= (x_4 + \frac{1}{2}) \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$a(x_4 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4a)	O II
$\mathbf{B}_{16}$	$= -(x_4 - \frac{1}{2}) \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_4 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	O II

References

- [1] M. Marezio, *The Crystal Structure of LiGaO₂*, Acta Cryst. **18**, 481–484 (1965), doi:10.1107/S0365110X65001068.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.