

α -LiIO₃ Structure:

ABC3_hP10_173_b_a_c-001


This structure previously used the label(s) **ABC3_hP10_173_b_a_c**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/DF6Y>

https://aflow.org/prototype-encyclopedia/ABC3_hP10_173_b_a_c-001

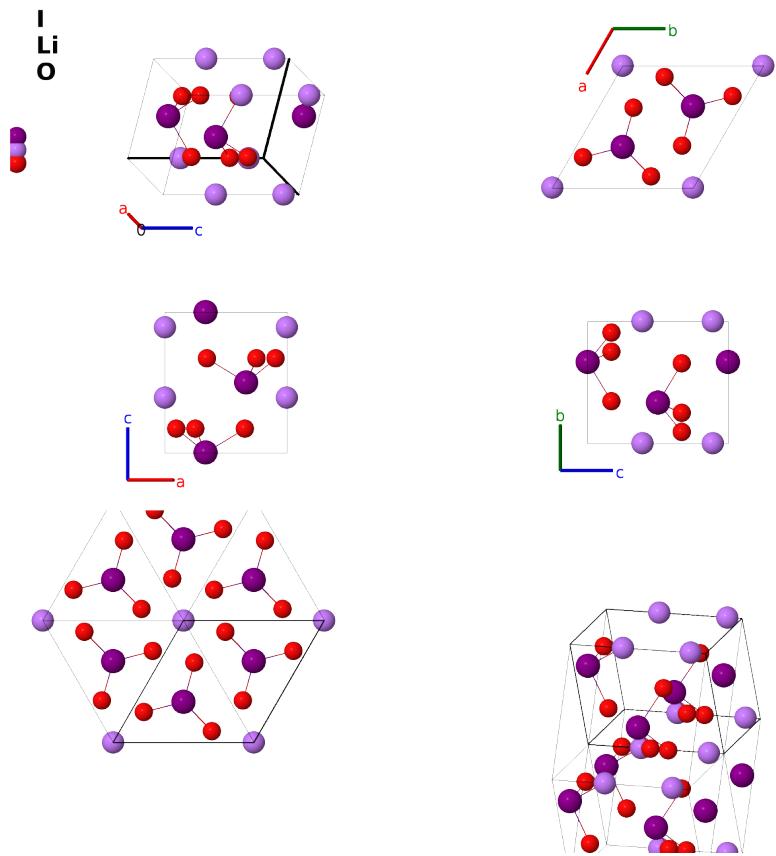

Prototype	ILiO ₃
AFLOW prototype label	ABC3_hP10_173_b_a_c-001
ICSD	14377
CCDC	1595762
Pearson symbol	hP10
Space group number	173
Space group symbol	$P6_3$


AFLOW prototype command `aflow --proto=ABC3_hP10_173_b_a_c-001`
 `--params=a, c/a, z1, z2, x3, y3, z3`

- LiIO₃ is known to exist in three forms:
- α -LiIO₃, stable below 470K:
 - (Zachariasen, 1931) originally determined that the structure of α -LiIO₃ was in space group $P6_322$ #182, which (Hermann, 1937) designated *Strukturbericht E2₃*.
 - (Rosenzweig, 1966) subsequently determined that this structure was incorrect because of the small sample size, and determined that the true structure was in space group $P6_3$ #173. (this structure)
- β -LiIO₃, stable from 573K up to the melting point at 708K.
- γ -LiIO₃, stable between the α - and β -phases, with an orthorhombic structure in space group $Pna2_1$ #33.
- The ICSD entry uses $a = 5.485\text{\AA}$ rather than the value $5.1815\text{\AA}$ found in (Rosenzweig, 1966). This is perhaps influenced by (De Boer, 1966) (ICSD 14344) and the original work of (Zachariasen, 1931), who both found values nearer $5.48\text{\AA}$. For now we will continue to use $5.1815\text{\AA}$.

Hexagonal primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}} \end{aligned}$$

$\mathbf{a}_1 \mathbf{a}_2 \mathbf{a}_3$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= z_1 \mathbf{a}_3$	$=$	$c z_1 \hat{\mathbf{z}}$	(2a)	Li I
$\mathbf{B}_2$	$= (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$c (z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(2a)	Li I
$\mathbf{B}_3$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c z_2 \hat{\mathbf{z}}$	(2b)	I I
$\mathbf{B}_4$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c (z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(2b)	I I
$\mathbf{B}_5$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$\frac{1}{2}a (x_3 + y_3) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a (x_3 - y_3) \hat{\mathbf{y}} + c z_3 \hat{\mathbf{z}}$	(6c)	O I
$\mathbf{B}_6$	$= -y_3 \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$\frac{1}{2}a (x_3 - 2y_3) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a x_3 \hat{\mathbf{y}} + c z_3 \hat{\mathbf{z}}$	(6c)	O I
$\mathbf{B}_7$	$= -(x_3 - y_3) \mathbf{a}_1 - x_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$-\frac{1}{2}a (2x_3 - y_3) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a y_3 \hat{\mathbf{y}} + c z_3 \hat{\mathbf{z}}$	(6c)	O I
$\mathbf{B}_8$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-\frac{1}{2}a (x_3 + y_3) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a (x_3 - y_3) \hat{\mathbf{y}} + c (z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(6c)	O I
$\mathbf{B}_9$	$= y_3 \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a (-x_3 + 2y_3) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a x_3 \hat{\mathbf{y}} + c (z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(6c)	O I
$\mathbf{B}_{10}$	$= (x_3 - y_3) \mathbf{a}_1 + x_3 \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a (2x_3 - y_3) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a y_3 \hat{\mathbf{y}} + c (z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(6c)	O I

References

- [1] A. Rosenzweig and B. Morosin, *A reinvestigation of the crystal structure of LiIO₃*, Acta Cryst. **20**, 758–761 (1966), doi:10.1107/S0365110X66001804.
- [2] W. H. Zachariasen and F. A. Barta, *Crystal Structure of Lithium Iodate*, Phys. Rev. **37**, 1626–1630 (1931), doi:10.1103/PhysRev.37.1626.

- [3] C. Hermann, O. Lohrmann, and H. Philipp, eds., *Strukturbericht Band II 1928-1932* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1937).
- [4] J. L. D. Boer, F. van Bolhuis, and R. V. Olthof-Hazekamp, *Re-investigation of the crystal structure of lithium iodate*, *Acta Crystallographica* **21**, 841–843 (1966), doi:10.1107/S0365110X66004031.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, *Comput. Mater. Sci.* **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.