

KBrO₃ (*G*₀₇) Structure: ABC3_hR5_160_a_a_b-001


This structure previously used the label(s) `ABC3_hR5_160_a_a_b.KBrO3`. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/0ZSQ>

https://aflow.org/prototype-encyclopedia/ABC3_hR5_160_a_a_b-001

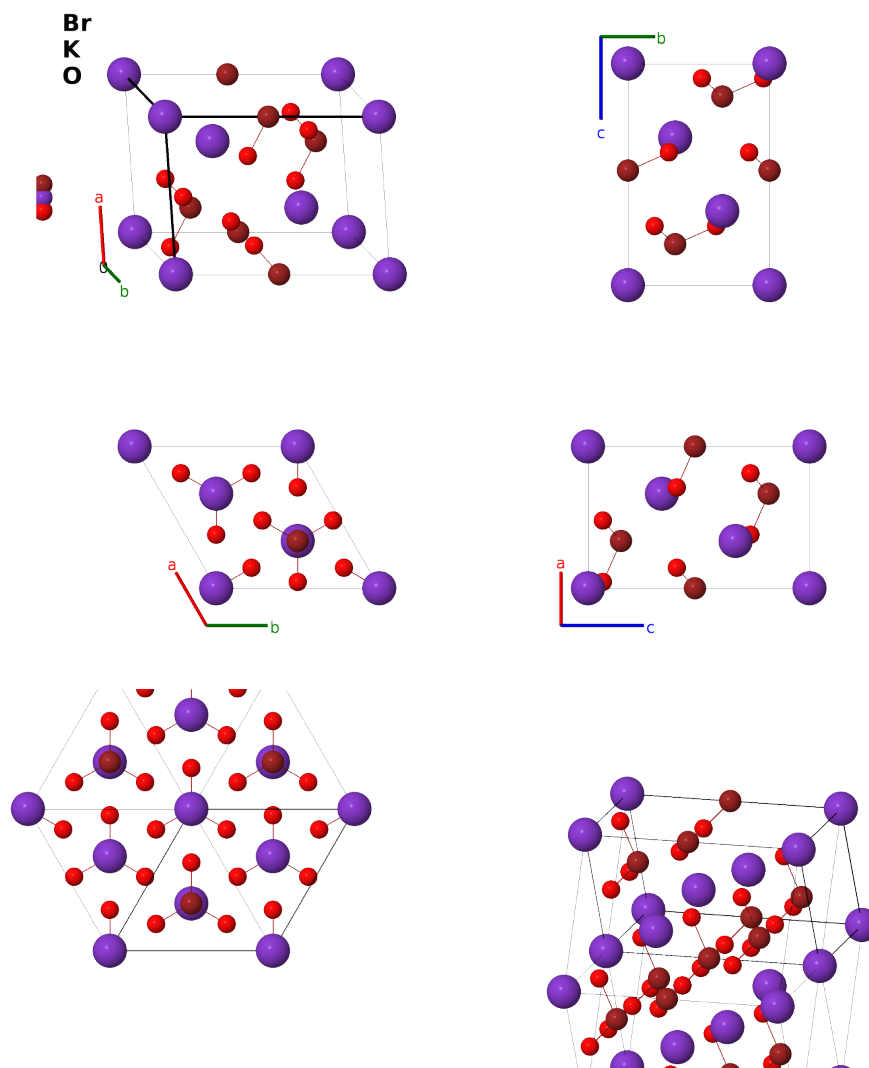

Prototype	BrKO ₃
AFLOW prototype label	ABC3_hR5_160_a_a_b-001
Strukturbericht designation	<i>G</i> ₀₇
ICSD	47173

CCDC	1614487
Pearson symbol	hR5
Space group number	160
Space group symbol	$R\bar{3}m$
AFLOW prototype command	aflow --proto=ABC3_hR5_160_a_a_b-001 --params= $a, c/a, x_1, x_2, x_3, z_3$


Other compounds with this structure

AgBaI₃, AsAlO₃, AsGaO₃, AsInO₃, AsYO₃, BaTiO₃, BiFeO₃, BiYO₃, CsBrO₃, CsClO₃, CsGeBr₃, CsGeCl₃, CsGeI₃, CsIO₃, CsMnN₃, CsSnI₃, CsTaO₃, FeBiO₃, Ge₂O₃, GePbO₃, GeSnO₃, GeTiO₃, HeNH₃, KBrO₃, KClO₃, KIO₃, KNbO₃, LaAlO₃, LaCoO₃, LaWN₃, LiUO₃, PbSnO₃, PrCoO₃, RbBrO₃, RbClO₃, RbIO₃, RbNO₃, RbNbO₃, SbAlO₃, SbGaO₃, SbInO₃, SbYO₃, Si₂O₃, TlBrO₃, TlClO₃, TlIO₃

- γ -KNO₃ and KBrO₃ ($G0_7$) have the same AFLOW prototype label, ABC3_hR5_160_a.a.b. They are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.
- Hexagonal settings rhombohedral structures can be obtained with the option `--hex`.

Rhombohedral primitive vectors

$$\begin{aligned}
 \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\
 \mathbf{a}_2 &= \frac{1}{\sqrt{3}}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\
 \mathbf{a}_3 &= -\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}}
 \end{aligned}$$

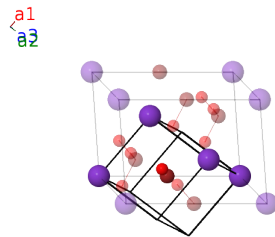

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + x_1 \mathbf{a}_3$	$=$	$cx_1 \hat{\mathbf{z}}$	(1a)	Br I
$\mathbf{B}_2$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$cx_2 \hat{\mathbf{z}}$	(1a)	K I
$\mathbf{B}_3$	$= x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_3 - z_3) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_3 - z_3) \hat{\mathbf{y}} + \frac{1}{3}c(2x_3 + z_3) \hat{\mathbf{z}}$	(3b)	O I
$\mathbf{B}_4$	$= z_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$-\frac{1}{2}a(x_3 - z_3) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a(x_3 - z_3) \hat{\mathbf{y}} + \frac{1}{3}c(2x_3 + z_3) \hat{\mathbf{z}}$	(3b)	O I
$\mathbf{B}_5$	$= x_3 \mathbf{a}_1 + z_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$-\frac{1}{\sqrt{3}}a(x_3 - z_3) \hat{\mathbf{y}} + \frac{1}{3}c(2x_3 + z_3) \hat{\mathbf{z}}$	(3b)	O I

References

- [1] D. H. Templeton and L. K. Templeton, *Tensor X-ray optical properties of the bromate ion*, Acta Crystallogr. Sect. A pp. 133–142 (1985), doi:10.1107/S0108767385000277.

Found in

- [1] D. Santamaría-Pérez, R. Chulia-Jordan, P. Rodríguez-Hernández, and A. M. noz, *Crystal behavior of potassium bromate under compression*, Acta Crystallogr. Sect. B **71**, 798–804 (2015), doi:10.1107/S2052520615018156.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.