

BaNiSn₃ Structure:

ABC3_tI10_107_a_a_ab-001


This structure previously used the label(s) **ABC3_tI10_107_a_a_ab**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/N3SR>

https://aflow.org/prototype-encyclopedia/ABC3_tI10_107_a_a_ab-001

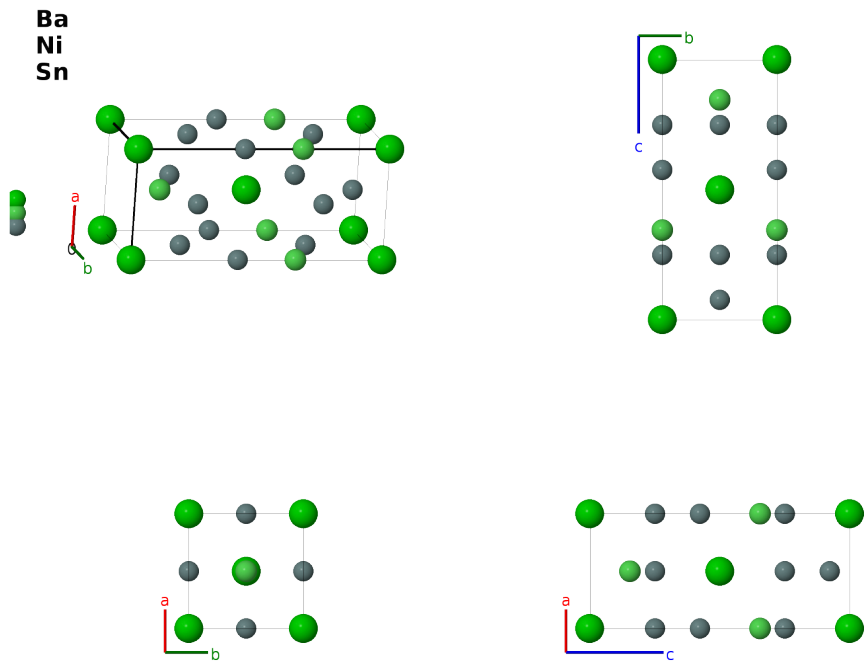

Prototype	BaNiSn ₃
AFLOW prototype label	ABC3_tI10_107_a_a_ab-001
ICSD	58662
CCDC	1622667
Pearson symbol	tI10
Space group number	107
Space group symbol	<i>I4mm</i>
AFLOW prototype command	<code>aflow --proto=ABC3_tI10_107_a_a_ab-001</code> <code>--params=a, c/a, z₁, z₂, z₃, z₄</code>


Other compounds with this structure

BaPdSn₃, BaPtSn₃, CeCuAl₃, EuPdGe₃, EuRhGe₃, LaOsSb₃, SrIrAl₃, SrNiSn₃, SrPdAl₃, SrPtAl₃

- This is a ternary form of the $D1_3$ (BaAl₄) structure. The atomic positions in both conventional cells are approximately the same, but the distribution of the atoms on those sites and the resulting relaxation leads to a different structure.
- Although (Dörrscheidt, 1978) give the structural information for BaPtSn₃ before that of BaNiSn₃, (Shatruk, 2019) and others list BaNiSn₃ as the prototype for this structure.
- Space group $I4mm$ #107 does not specify the origin of the z -axis. (Dörrscheidt, 1978) places the barium atom at the origin.

Body-centered Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}c \hat{\mathbf{z}}\end{aligned}$$

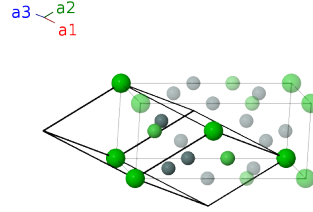

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= z_1 \mathbf{a}_1 + z_1 \mathbf{a}_2$	$=$	$cz_1 \hat{\mathbf{z}}$	(2a)	Ba I
$\mathbf{B}_2$	$= z_2 \mathbf{a}_1 + z_2 \mathbf{a}_2$	$=$	$cz_2 \hat{\mathbf{z}}$	(2a)	Ni I
$\mathbf{B}_3$	$= z_3 \mathbf{a}_1 + z_3 \mathbf{a}_2$	$=$	$cz_3 \hat{\mathbf{z}}$	(2a)	Sn I
$\mathbf{B}_4$	$= \left(z_4 + \frac{1}{2}\right) \mathbf{a}_1 + z_4 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4b)	Sn II
$\mathbf{B}_5$	$= z_4 \mathbf{a}_1 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + cz_4 \hat{\mathbf{z}}$	(4b)	Sn II

References

- [1] W. Dörrscheidt and H. Schäfer, *Die struktur des BaPtSn₃, BaNiSn₃ und SrNiSn₃ und ihre verwandtschaft zum ThCr₂Si₂-strukturtyp*, J. Less-Common Met. **58**, 209–216 (1978), doi:10.1016/0022-5088(78)90202-3.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.