

Ullmanite (NiSSb, $F0_1$) Structure: ABC_cP12_198_a_a_a-001


This structure previously used the label(s) **ABC_cP12_198_a_a_a**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/VHP8>

https://aflow.org/prototype-encyclopedia/ABC_cP12_198_a_a_a-001

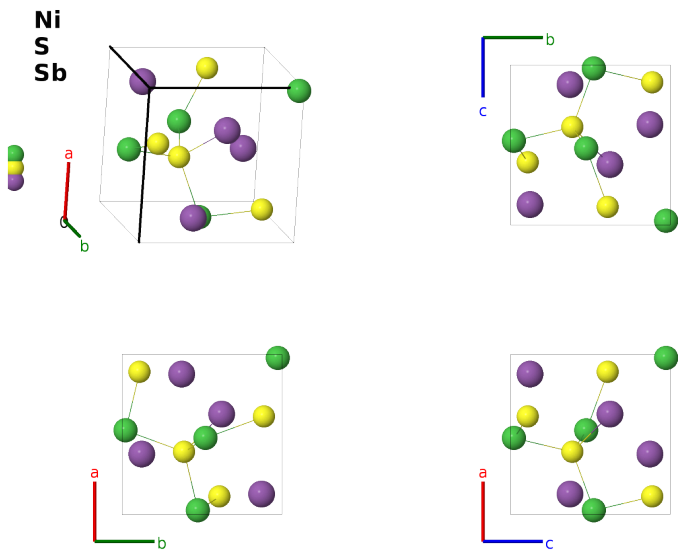

Prototype	NiSSb
AFLOW prototype label	ABC_cP12_198_a_a_a-001
<i>Strukturbericht</i> designation	$F0_1$
Mineral name	ullmanite
ICSD	44606
CCDC	1613974
Pearson symbol	cP12
Space group number	198
Space group symbol	$P2_13$
AFLOW prototype command	<code>aflow --proto=ABC_cP12_198_a_a_a-001</code> <code>--params=a, x_1, x_2, x_3</code>


Other compounds with this structure

AlAuBa, AlAuCa, AsBaPt, AsCoS (cobaltite), AsPdS, AsPdSe, AuBaGa, AuCaGa, AuCaIn, AuGaSr, AuInSr, BiIrS, BiIrSe, BiNiSe, BiPdSe, BiPtSe, BiRhS, BiRhSe, CaPtSi, CrPtSb, EuPtSi, IrLaSi, IrPSe, IrSSb, IrSSe, IrSbSe, PRhSe, PdSSb, PdSbSe, RhSSb, RhSbSe, (Co, Ni)SbS

- (Ewald, 1928) originally designated CoAsS as *Strukturbericht F1*. This was later changed to *F0₁*. We follow (Parthé, 1993) in using NiSbS as the prototype for this structure.
- The Sb (4a) Wyckoff parameter (x_3) has been corrected from 0.875 to 0.625, which matches the bonding distances given by (Y. Takéuchi, 1957) (corrected on 2021/05/10).

Simple Cubic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= a \hat{\mathbf{z}}\end{aligned}$$

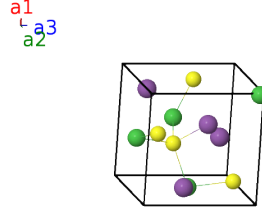

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + x_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + ax_1 \hat{\mathbf{y}} + ax_1 \hat{\mathbf{z}}$	(4a)	Ni I
$\mathbf{B}_2$	$= -\left(x_1 - \frac{1}{2}\right) \mathbf{a}_1 - x_1 \mathbf{a}_2 + \left(x_1 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{x}} - ax_1 \hat{\mathbf{y}} + a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4a)	Ni I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 + \left(x_1 + \frac{1}{2}\right) \mathbf{a}_2 - \left(x_1 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{y}} - a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4a)	Ni I
$\mathbf{B}_4$	$= \left(x_1 + \frac{1}{2}\right) \mathbf{a}_1 - \left(x_1 - \frac{1}{2}\right) \mathbf{a}_2 - x_1 \mathbf{a}_3$	$=$	$a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{y}} - ax_1 \hat{\mathbf{z}}$	(4a)	Ni I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(4a)	S I
$\mathbf{B}_6$	$= -\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 - x_2 \mathbf{a}_2 + \left(x_2 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} + a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4a)	S I
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + \left(x_2 + \frac{1}{2}\right) \mathbf{a}_2 - \left(x_2 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{y}} - a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4a)	S I
$\mathbf{B}_8$	$= \left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 - \left(x_2 - \frac{1}{2}\right) \mathbf{a}_2 - x_2 \mathbf{a}_3$	$=$	$a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(4a)	S I
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}}$	(4a)	Sb I
$\mathbf{B}_{10}$	$= -\left(x_3 - \frac{1}{2}\right) \mathbf{a}_1 - x_3 \mathbf{a}_2 + \left(x_3 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + a\left(x_3 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4a)	Sb I
$\mathbf{B}_{11}$	$= -x_3 \mathbf{a}_1 + \left(x_3 + \frac{1}{2}\right) \mathbf{a}_2 - \left(x_3 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + a\left(x_3 + \frac{1}{2}\right) \hat{\mathbf{y}} - a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4a)	Sb I
$\mathbf{B}_{12}$	$= \left(x_3 + \frac{1}{2}\right) \mathbf{a}_1 - \left(x_3 - \frac{1}{2}\right) \mathbf{a}_2 - x_3 \mathbf{a}_3$	$=$	$a\left(x_3 + \frac{1}{2}\right) \hat{\mathbf{x}} - a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{y}} - ax_3 \hat{\mathbf{z}}$	(4a)	Sb I

References

- [1] Y. Takéuchi, *The Absolute Structure of Ullmanite, NiSbS*, Mineralogical Journal **2**, 90–102 (1957), doi:10.2465/minerj1953.2.90.
- [2] P. P. Ewald and C. Hermann, eds., *Strukturbericht 1913-1928* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1931).
- [3] Parthé, L. Gelato, B. Chabot, M. Penso, K. Cenzula, and R. Gladyshevskii, *Standardized Data and Crystal Chemical Characterization of Inorganic Structure Types, Gmelin Handbook of Inorganic and Organometallic Chemistry*, vol. 2 (Springer-Verlag, Berlin, Heidelberg, 1993), 8 edn., doi:10.1007/978-3-662-02909-1_3.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017