

Pararealgar (AsS) Structure: AB_mP32_14_4e_4e-001


This structure previously used the label(s) **AB_mP32_14_4e_4e.pararealgar**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/WH80>

https://aflow.org/prototype-encyclopedia/AB_mP32_14_4e_4e-001

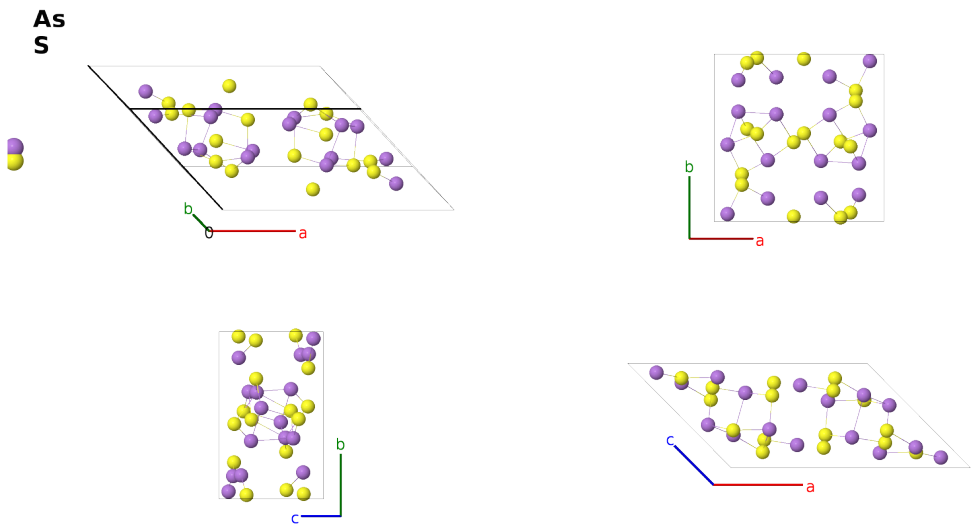


Prototype	AsS
AFLOW prototype label	AB_mP32_14_4e_4e-001
Mineral name	pararealgar
ICSD	80125
CCDC	1640351
Pearson symbol	mP32
Space group number	14
Space group symbol	$P2_1/c$
AFLOW prototype command	<pre>aflow --proto=AB_mP32_14_4e_4e-001 --params=a,b/a,c/a,β,x_1,y_1,z_1,x_2,y_2,z_2,x_3,y_3,z_3,x_4,y_4,z_4,x_5,y_5,z_5,x_6,y_6,z_6,x_7,y_7,z_7,x_8,y_8,z_8</pre>

Other compounds with this structure
AsSe

- Realgar (B_l) transforms to pararealgar on exposure to visible light with wavelengths in the range 500-670 nm. (Douglass, 1992)
- Realgar (AsS, B_l), pararealgar (AsS), NS, and NaGe all have the same AFLOW prototype label, AB_mP32_14_4e.4e. They are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Monoclinic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}} \end{aligned}$$

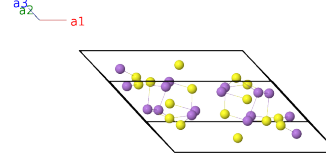

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	As I
$\mathbf{B}_2$	$-x_1 \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As I
$\mathbf{B}_3$	$-x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	=	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	As I
$\mathbf{B}_4$	$x_1 \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As I
$\mathbf{B}_5$	$x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	As II
$\mathbf{B}_6$	$-x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As II
$\mathbf{B}_7$	$-x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	As II
$\mathbf{B}_8$	$x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As II
$\mathbf{B}_9$	$x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	As III
$\mathbf{B}_{10}$	$-x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As III
$\mathbf{B}_{11}$	$-x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	As III
$\mathbf{B}_{12}$	$x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As III
$\mathbf{B}_{13}$	$x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	As IV
$\mathbf{B}_{14}$	$-x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As IV
$\mathbf{B}_{15}$	$-x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	=	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	As IV
$\mathbf{B}_{16}$	$x_4 \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	As IV
$\mathbf{B}_{17}$	$x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	=	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	S I
$\mathbf{B}_{18}$	$-x_5 \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	=	$-(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	S I
$\mathbf{B}_{19}$	$-x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	=	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	S I

$$\begin{aligned}
\mathbf{B}_{20} &= x_5 \mathbf{a}_1 - \left(y_5 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_5 + \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} (ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - \\ b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S I} \\
\mathbf{B}_{21} &= x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3 = \begin{pmatrix} (ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S II} \\
\mathbf{B}_{22} &= -x_6 \mathbf{a}_1 + \left(y_6 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_6 - \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} -(ax_6 + c(z_6 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + \\ b(y_6 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S II} \\
\mathbf{B}_{23} &= -x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3 = \begin{pmatrix} -(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S II} \\
\mathbf{B}_{24} &= x_6 \mathbf{a}_1 - \left(y_6 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_6 + \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} (ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - \\ b(y_6 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S II} \\
\mathbf{B}_{25} &= x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3 = \begin{pmatrix} (ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S III} \\
\mathbf{B}_{26} &= -x_7 \mathbf{a}_1 + \left(y_7 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_7 - \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} -(ax_7 + c(z_7 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + \\ b(y_7 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S III} \\
\mathbf{B}_{27} &= -x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3 = \begin{pmatrix} -(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S III} \\
\mathbf{B}_{28} &= x_7 \mathbf{a}_1 - \left(y_7 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_7 + \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} (ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - \\ b(y_7 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S III} \\
\mathbf{B}_{29} &= x_8 \mathbf{a}_1 + y_8 \mathbf{a}_2 + z_8 \mathbf{a}_3 = \begin{pmatrix} (ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} + cz_8 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S IV} \\
\mathbf{B}_{30} &= -x_8 \mathbf{a}_1 + \left(y_8 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_8 - \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} -(ax_8 + c(z_8 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + \\ b(y_8 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_8 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S IV} \\
\mathbf{B}_{31} &= -x_8 \mathbf{a}_1 - y_8 \mathbf{a}_2 - z_8 \mathbf{a}_3 = \begin{pmatrix} -(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} - cz_8 \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S IV} \\
\mathbf{B}_{32} &= x_8 \mathbf{a}_1 - \left(y_8 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_8 + \frac{1}{2}\right) \mathbf{a}_3 = \begin{pmatrix} (ax_8 + c(z_8 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - \\ b(y_8 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_8 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} & (4e) & \text{S IV}
\end{aligned}$$

References

- [1] P. Bonazzi, S. Menchetii, and G. Pratesi, *The crystal structure of pararealgar, As₄S₄*, Am. Mineral. **80**, 400–403 (1995), doi:10.2138/am-1995-3-423.
- [2] D. L. Douglass, C. Shing, and D. Wang, *The light-induced alteration of realgar to pararealgar*, Am. Mineral. **77**, 1266–1274 (1992).

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.