

α -LiSn Structure:

AB_mP6_10_bn_cm-001


This structure previously used the label(s) **AB_mP6_10_en_am**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/QVV1>

https://aflow.org/prototype-encyclopedia/AB_mP6_10_bn_cm-001

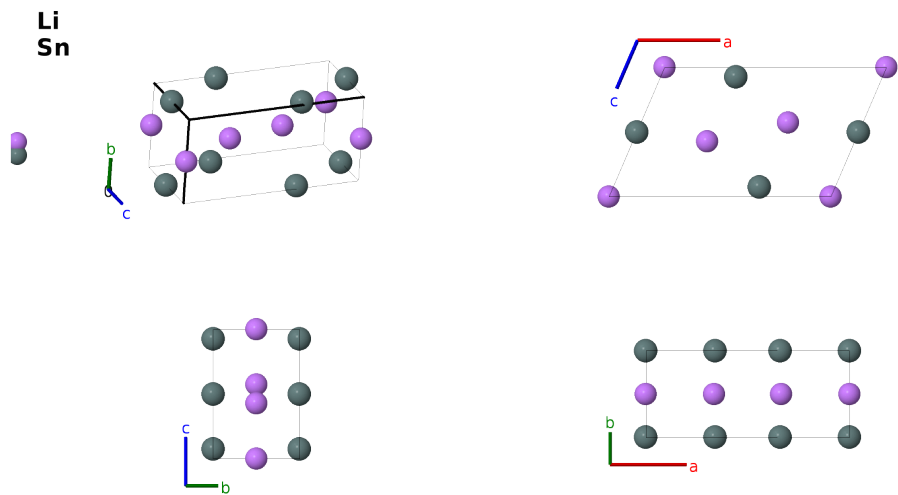


Prototype	LiSn
AFLOW prototype label	AB_mP6_10_bn_cm-001
ICSD	104782
CCDC	1662683
Pearson symbol	mP6
Space group number	10
Space group symbol	$P2/m$
AFLOW prototype command	<code>aflow --proto=AB_mP6_10_bn_cm-001</code> <code>--params=a, b/a, c/a, β, x_3, z_3, x_4, z_4</code>

- This is the low-temperature structure of LiSn. Above 470K LiSn may transform into the tetragonal β -LiSn structure (Villars, 2018). This structure is apparently metastable at room temperature (Blase, 1990).
- The AFLOW prototype label protocol moves the origin so that the Li I atom is on the (1b) Wyckoff site rather than the (1a) site used by (Müller, 1973).

Simple Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$

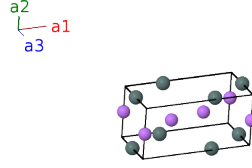

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2} b \hat{\mathbf{y}}$	(1b)	Li I
$\mathbf{B}_2$	$= \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} c \cos \beta \hat{\mathbf{x}} + \frac{1}{2} c \sin \beta \hat{\mathbf{z}}$	(1c)	Sn I
$\mathbf{B}_3$	$= x_3 \mathbf{a}_1 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(2m)	Sn II
$\mathbf{B}_4$	$= -x_3 \mathbf{a}_1 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(2m)	Sn II
$\mathbf{B}_5$	$= x_4 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + \frac{1}{2} b \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(2n)	Li II
$\mathbf{B}_6$	$= -x_4 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + \frac{1}{2} b \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(2n)	Li II

References

- [1] W. Müller and H. Schäfer, *Die Kristallstruktur der Phase LiSn*, Z. Naturforsch. B **28**, 246–248 (1973), doi:10.1515/znb-1973-5-604.
- [2] P. Villars, H. Okamoto, and K. Cenzual, eds., *ASM Alloy Phase Diagram Database* (ASM International, 2018), chap. Lithium-Tin Binary Phase Diagram (1998 Sangster J.). Copyright ©2006-2018 ASM International.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043