

CrB (*B33*) Structure:

AB_oC8_63_c_c-001


This structure previously used the label(s) **AB_oC8_63_c_c**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/QWV1>

https://aflow.org/prototype-encyclopedia/AB_oC8_63_c_c-001

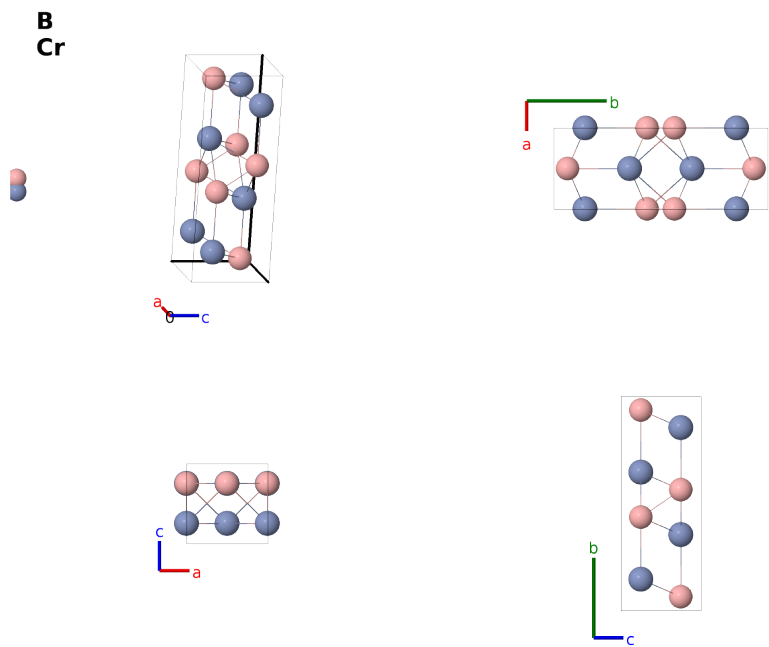

Prototype	BCr
AFLOW prototype label	AB_oC8_63_c_c-001
<i>Strukturbericht</i> designation	<i>B33</i>
ICSD	44250
CCDC	1613667
Pearson symbol	oC8
Space group number	63
Space group symbol	<i>Cmcm</i>
AFLOW prototype command	<code>aflow --proto=AB_oC8_63_c_c-001</code> <code>--params=<i>a</i>,<i>b</i>/<i>a</i>,<i>c</i>/<i>a</i>,<i>y</i>₁,<i>y</i>₂</code>


Other compounds with this structure

AgCa, AlHf, AlTh, AlY, AlZr, AuGd, BNb, BNi, BTa, BV, BaPb, CaGe, CaSi, CaSn, CeNi, CePt, CeRh, CoTh, DyGa, DyGe, ErNi, GaGd, GaPr, GdGe, GeHo, GeNi, GePr, HfNi, HfPt, HoNi, ITl, IrTh, LaNi, LaPt, LaRh, LuNi, NdNi, NdRh, NiPr, NiPu, NiSm, NiTb, NiTm, NiZr, PrRh, PtTh, PtZr, RhTh, RuTh, SiSr, SnSr, SiY, (Ge, Si)Ho

- (Gottfried, 1938) originally gave the *B33 Strukturbericht* designation to thallium iodide, TlI. Later, (Smithells, 1955) gave CrB structure the new designation B_f . These structures are identical, and we follow (Parthé, 1993) in using *B33* to designate both structures.
- Removing either the Cr or B atoms transforms this into the α -U (A20) structure.
- β -SnS and CrB (*B33*) have the same AFLOW label, AB_oC8_63_c.c. The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Base-centered Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

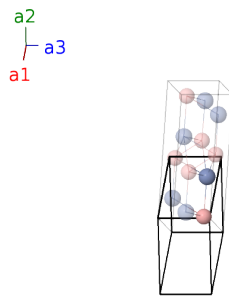

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$by_1 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4c)	B I
$\mathbf{B}_2$	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-by_1 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4c)	B I
$\mathbf{B}_3$	$= -y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$by_2 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4c)	Cr I
$\mathbf{B}_4$	$= y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-by_2 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4c)	Cr I

References

- [1] S. Okada, T. Atoda, and I. Higashi, *Structural investigation of Cr_2B_3 , Cr_3B_4 , and CrB by single-crystal diffractometry*, J. Solid State Chem. **68**, 61–67 (1987), doi:10.1016/0022-4596(87)90285-4.
- [2] C. Gottfried, ed., *Strukturbericht Band IV 1936* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1938).
- [3] C. J. Smithells, *Metals Reference Book* (Butterworths Scientific, London, 1955), second edn.
- [4] E. Parthé, L. Gelato, B. Chabot, M. Penso, K. Cenzula, and R. Gladyshevskii, *Standardized Data and Crystal Chemical Characterization of Inorganic Structure Types, Gmelin Handbook of Inorganic and Organometallic Chemistry*, vol. 2 (Springer-Verlag, Berlin, Heidelberg, 1993), 8 edn., doi:10.1007/978-3-662-02909-1_3.

Found in

- [1] P. Villars, *CrB Crystal Structure* (2016). PAULING FILE in: Inorganic Solid Phases, SpringerMaterials (online database), Springer, Heidelberg (ed.) SpringerMaterials.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017