

α -IrV Structure:

AB_oC8_65_g-j-001


This structure previously used the label(s) **AB_oC8_65_j.g**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/S2CY>

https://aflow.org/prototype-encyclopedia/AB_oC8_65_g-j-001

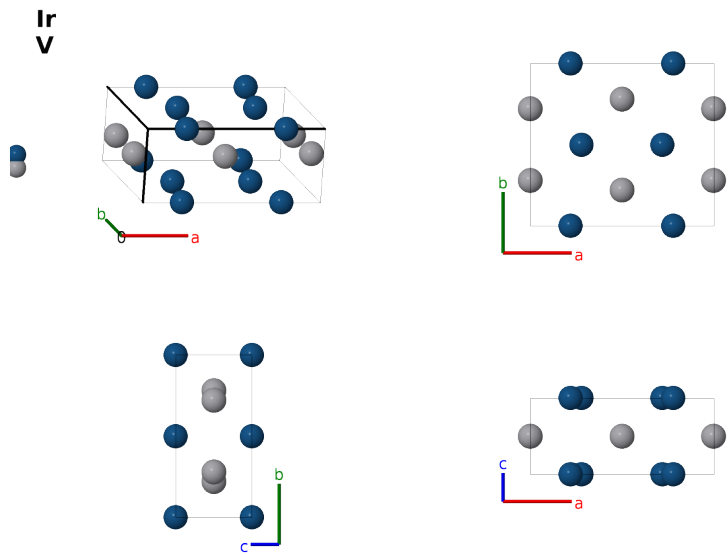

Prototype	IrV
AFLOW prototype label	AB.oC8_65_g-j-001
ICSD	104590
CCDC	1662502
Pearson symbol	oC8
Space group number	65
Space group symbol	$Cmmm$
AFLOW prototype command	<code>aflow --proto=AB_oC8_65_g-j-001</code> <code>--params=a, b/a, c/a, x₁, y₂</code>


Other compounds with this structure

AuNa, CdTe, RhV

Base-centered Orthorhombic primitive vectors

a₃
a₂
a₁

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	$x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2$	$=$	$ax_1 \hat{\mathbf{x}}$	(4g) Ir I
$\mathbf{B}_2$	$=$	$-x_1 \mathbf{a}_1 - x_1 \mathbf{a}_2$	$=$	$-ax_1 \hat{\mathbf{x}}$	(4g) Ir I
$\mathbf{B}_3$	$=$	$-y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$by_2 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4j) V I
$\mathbf{B}_4$	$=$	$y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-by_2 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4j) V I

References

- [1] B. C. Giessen and N. J. Grant, *New intermediate phases in transition metal systems, III*, Acta Cryst. **18**, 1080–1081 (1965), doi:10.1107/S0365110X65002566.

Found in

- [1] P. Villars and L. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases* (ASM International, Materials Park, OH, 1991), 2nd edn.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017