

α -FeSe Structure:

AB_oC8_67_a_g-001


This structure previously used the label(s) **AB_oC8_67_a_g.FeSe**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/JFD1>

https://aflow.org/prototype-encyclopedia/AB_oC8_67_a_g-001

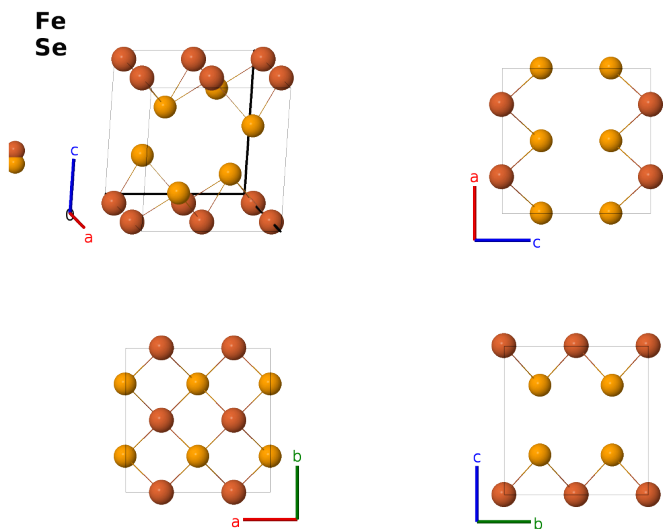


Prototype	FeSe
AFLOW prototype label	AB_oC8_67_a_g-001
ICSD	185465
CCDC	1694661
Pearson symbol	oC8
Space group number	67
Space group symbol	<i>Cmme</i>
AFLOW prototype command	<code>aflow --proto=AB_oC8_67_a_g-001 --params=a, b/a, c/a, z₂</code>

- We follow (Louca, 2010) in calling this α -FeSe. While some authorities list this as a prototype of α -PbO, we find that the difference in structures is enough to warrant giving FeSe its own prototype.
- (Louca, 2010) note that “the Se ion concentration is close to 1.”
- The data is presented for the structure at 7 K.

- The ICSD entry is from the (Lehman, 2010) conference proceedings.
- (Louca, 2010) find $a \approx b$. As with orthorhombic α -PbO and tetragonal ($B10$) PbO, this causes AFLOW to place this in the tetragonal $P4/nmm$ #129 space group if the default settings are used. The experimentally reported structure is only obtained if we use the command
- `afLOW --proto=AB_oC8_67_a_g --tolerance=0.001 --params=a,c/a,z2` .
- α -FeSe and α -PbO have the same AFLOW prototype label, AB_oC8.67_a.g. They are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Base-centered Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

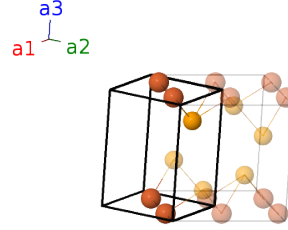

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{4} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2$	$=$	$\frac{1}{4}a \hat{\mathbf{x}}$	(4a)	Fe I
$\mathbf{B}_2$	$= \frac{3}{4} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2$	$=$	$\frac{3}{4}a \hat{\mathbf{x}}$	(4a)	Fe I
$\mathbf{B}_3$	$= \frac{3}{4} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4g)	Se I
$\mathbf{B}_4$	$= \frac{1}{4} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4g)	Se I

References

- [1] D. Louca, K. Horigane, A. Llobet, R. Arita, S. Ji, N. Katayama, S. Konbu, K. Nakamura, T.-Y. Koo, P. Tong, and K. Yamada, *Local atomic structure of superconducting $\text{FeSe}_{1-x}\text{Te}_x$* , Phys. Rev. B **81**, 134524 (2010), doi:10.1103/PhysRevB.81.134524.
- [2] M. C. Lehman, A. Llobet, K. Horigane, and D. Louca, *The crystal structure of superconducting $\text{FeSe}_{1-x}\text{Te}_x$ by pulsed neutron diffraction*, J. Phys: Conf. Ser. **251**, 012009 (2010), doi:10.1088/1742-6596/251/1/012009.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043