

GeS (*B*16) Structure: AB_oP8_62_c_c-001


This structure previously used the label(s) **AB_oP8_62_c_c.GeS**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/Y0CA>

https://aflow.org/prototype-encyclopedia/AB_oP8_62_c_c-001

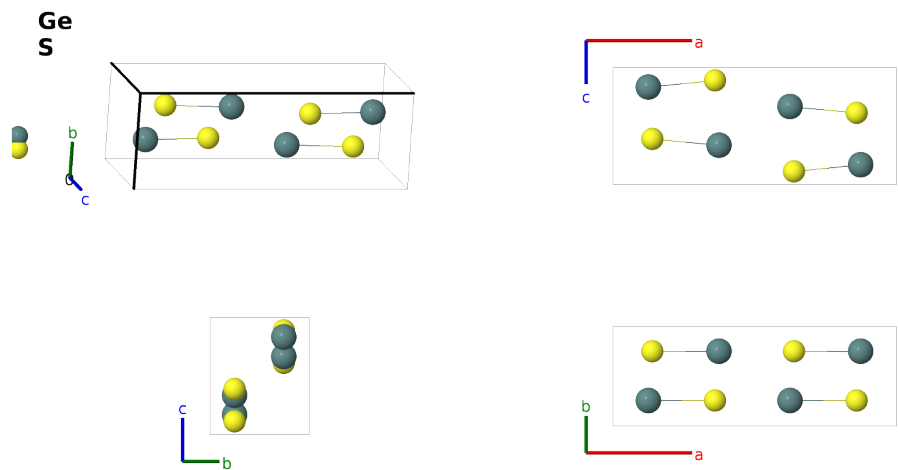

Prototype	GeS
AFLOW prototype label	AB_oP8_62_c_c-001
<i>Strukturbericht</i> designation	<i>B</i> 16
ICSD	38165
CCDC	1608874
Pearson symbol	oP8
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	<code>aflow --proto=AB_oP8_62_c_c-001</code> <code>--params=<i>a</i>,<i>b/a</i>,<i>c/a</i>,<i>x</i>₁,<i>z</i>₁,<i>x</i>₂,<i>z</i>₂</code>


Other compounds with this structure

GeSe, GeTe, PbS, PbSe, SnS, SnSe, SnTe

- Also see the closely related *B*29 (SnS) structure. (Parthé, 1993) prefers the *B*16 designation for both structures.

- FeAs (*B*14), GeS (*B*16), FeB (*B*27), SnS (*B*29), MnP (*B*31), and η -NiSi (*B*_d) all share the same AFLOW label, AB_oP8_62_c_c. The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors
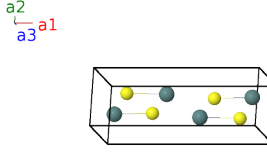
$$\begin{aligned} \mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}} \end{aligned}$$


Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	Ge I
$\mathbf{B}_2$	$= -\left(x_1 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_1 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_1 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Ge I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	Ge I
$\mathbf{B}_4$	$= \left(x_1 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_1 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_1 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Ge I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_6$	$= -\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_2 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_2 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_8$	$= \left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_2 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_2 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	S I

References

- [1] W. H. Zachariasen, *The Crystal Lattice of Germano Sulphide, GeS*, Phys. Rev. **40**, 917–922 (1932), doi:10.1103/PhysRev.40.917.
- [2] E. Parthé, L. Gelato, B. Chabot, M. Penso, K. Cenzula, and R. Gladyshevskii, *Standardized Data and Crystal Chemical Characterization of Inorganic Structure Types, Gmelin Handbook of Inorganic and Organometallic Chemistry*, vol. 2 (Springer-Verlag, Berlin, Heidelberg, 1993), 8 edn., doi:10.1007/978-3-662-02909-1_3.

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017