

MnP (*B*31) Structure: AB_oP8_62_c_c-002


This structure previously used the label(s) **AB_oP8_62_c_c.MnP**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/36ZK>

https://aflow.org/prototype-encyclopedia/AB_oP8_62_c_c-002

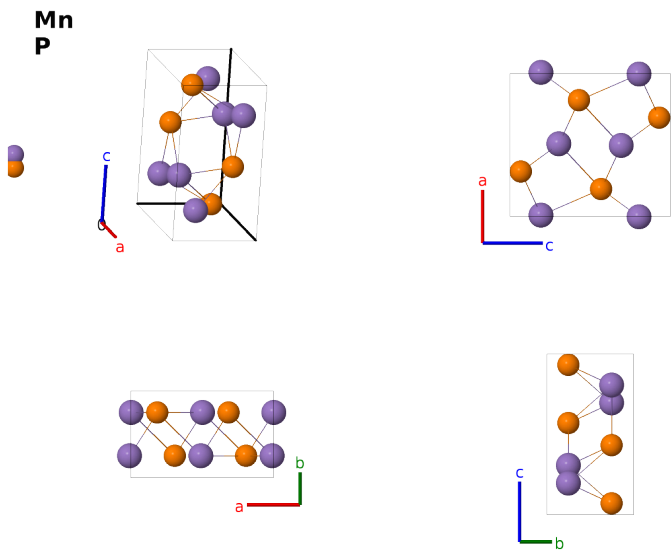

Prototype	MnP
AFLOW prototype label	AB_oP8_62_c_c-002
<i>Strukturbericht</i> designation	<i>B</i> 31
ICSD	76091
CCDC	1636723
Pearson symbol	oP8
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	<code>aflow --proto=AB_oP8_62_c_c-002</code> <code>--params=<i>a</i>, <i>b/a</i>, <i>c/a</i>, <i>x</i>₁, <i>z</i>₁, <i>x</i>₂, <i>z</i>₂</code>


Other compounds with this structure

AsCo, AsCr, AsFe, AsMn, AsRh, AsRu, AsV, AuGa, CoP, CrP, FeP, FeS, GeIr, GeNi, GePd, GePt, GeRh, IrSi, Nb_{1-x}S (HT), NiSi, PRu, PW, PdSi, PdSn, PtSi, RhSb, RhSi, SV, SeTi

- (Hermann, 1937) assigns the prototype FeAs and the Strukturbericht designation *B14* to this structure. This was superseded by the similar MnP structure in (Gottfried, 1937, pp. 17-18), where it is designated *B31*. (Parthé, 1993) prefers *B14*.
- We inadvertently used the wrong atomic coordinates in the previous version of this structure. These have now been corrected to match the 10K data of (Fjellvag, 1984).
- FeAs (*B14*), GeS (*B16*), FeB (*B27*), SnS (*B29*), MnP (*B31*), and η -NiSi (*B_d*) all share the same AFLOW label, AB_oP8_62_c_c. The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates		Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$		(4c)	Mn I
$\mathbf{B}_2$	$= -\left(x_1 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_1 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_1 + \frac{1}{2}\right) \hat{\mathbf{z}}$		(4c)	Mn I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$		(4c)	Mn I
$\mathbf{B}_4$	$= \left(x_1 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_1 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_1 - \frac{1}{2}\right) \hat{\mathbf{z}}$		(4c)	Mn I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$		(4c)	P I
$\mathbf{B}_6$	$= -\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_2 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_2 + \frac{1}{2}\right) \hat{\mathbf{z}}$		(4c)	P I
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$		(4c)	P I
$\mathbf{B}_8$	$= \left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_2 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_2 - \frac{1}{2}\right) \hat{\mathbf{z}}$		(4c)	P I

References

- [1] H. Fjellvåg and A. Kjekshus, *Magnetic and Structural Properties of Transition Metal Substituted MnP. I. $\text{Mn}_{1-t}\text{Co}_t\text{P}$ ($0.00 \leq t \leq 0.30$)*, Acta Chem. Scand. A **38**, 563–573 (1984), doi:10.3891/acta.chem.scand.38a-0563.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017