

β -SeTl (*B37*) Structure: AB_tI16_140_ab_h-001


This structure previously used the label(s) **AB_tI16_140_ab_h**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/BFE0>

https://aflow.org/prototype-encyclopedia/AB_tI16_140_ab_h-001

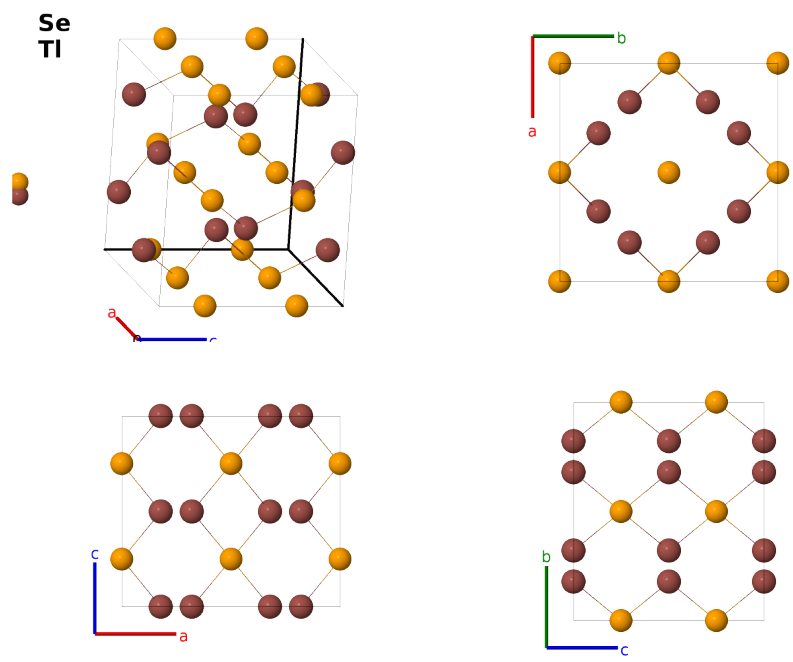

Prototype	SeTl
AFLOW prototype label	AB.tI16_140_ab_h-001
<i>Strukturbericht</i> designation	<i>B37</i>
ICSD	30219
CCDC	1604590
Pearson symbol	tI16
Space group number	140
Space group symbol	<i>I4/mcm</i>
AFLOW prototype command	<code>aflow --proto=AB_tI16_140_ab_h-001</code> <code>--params=<i>a, c/a, x₃</i></code>


Other compounds with this structure

InTe, STl, AlKTe₂, AlNaSe₂, AlNaTe₂, GaNaTe₂, GaTe₂Tl, InKTe₂, InNaTe₂, InS₂Te

- When $c = a$ and $x = 1/4$ the atoms are at the positions of the body-centered cubic (A2) lattice.
 - (Okamoto, 2011) identifies this as β -SeTl, stable from 188°C to the melting point at approximately 350°C. No crystallographic information on the ground-state α phase has been found.
 - The lattice constants presented here are from (Yadav, 1976), while the atomic positions and the ICSD entry are from (Ketelaar, 1939).
-

Body-centered Tetragonal primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}c \hat{\mathbf{z}} \end{aligned}$$

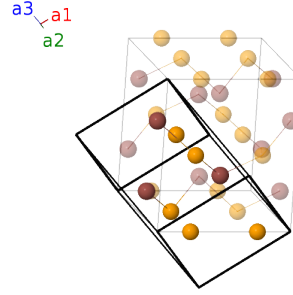

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{4} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2$	$=$	$\frac{1}{4}c \hat{\mathbf{z}}$	(4a)	Se I
$\mathbf{B}_2$	$= \frac{3}{4} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2$	$=$	$\frac{3}{4}c \hat{\mathbf{z}}$	(4a)	Se I
$\mathbf{B}_3$	$= \frac{3}{4} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4b)	Se II
$\mathbf{B}_4$	$= \frac{1}{4} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4b)	Se II
$\mathbf{B}_5$	$= \left(x_3 + \frac{1}{2}\right) \mathbf{a}_1 + x_3 \mathbf{a}_2 + \left(2x_3 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + a \left(x_3 + \frac{1}{2}\right) \hat{\mathbf{y}}$	(8h)	Tl I
$\mathbf{B}_6$	$= -\left(x_3 - \frac{1}{2}\right) \mathbf{a}_1 - x_3 \mathbf{a}_2 - \left(2x_3 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - a \left(x_3 - \frac{1}{2}\right) \hat{\mathbf{y}}$	(8h)	Tl I
$\mathbf{B}_7$	$= x_3 \mathbf{a}_1 - \left(x_3 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-a \left(x_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}}$	(8h)	Tl I
$\mathbf{B}_8$	$= -x_3 \mathbf{a}_1 + \left(x_3 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$a \left(x_3 + \frac{1}{2}\right) \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}}$	(8h)	Tl I

References

- [1] J. A. A. Ketelaar, W. H. t'Hart, M. Moerel, and D. Polder, *The Crystal Structure of TlSe, Thallous Thallic or Thalloic Selenide*, Z. Krystallogr. **101**, 396–406 (1939), doi:10.1524/zkri.1939.101.1.396.
- [2] R. Yadav, R. P. Ram, and S. Bhan, *On the Thallium-Selenium-Tellurium System*, Z. Metallkd. **67**, 173–177 (1976), doi:10.1515/ijmr-1976-670308.
- [3] H. Okamoto, *Se-Tl (Selenium-Thallium)*, J. Phase Eq. Diff. **32**, 570–571 (2011), doi:10.1007/s11669-011-9954-2.

Found in

- [1] P. Villars, *TlSe Crystal Structure* (2016). PAULING FILE in: Inorganic Solid Phases, SpringerMaterials (online database), Springer, Heidelberg (ed.) SpringerMaterials.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017