

MoB (B_g) Structure: AB_tI16_141_e_e-001


This structure previously used the label(s) **AB_tI16_141_e_e**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/B9A8>

https://aflow.org/prototype-encyclopedia/AB_tI16_141_e_e-001

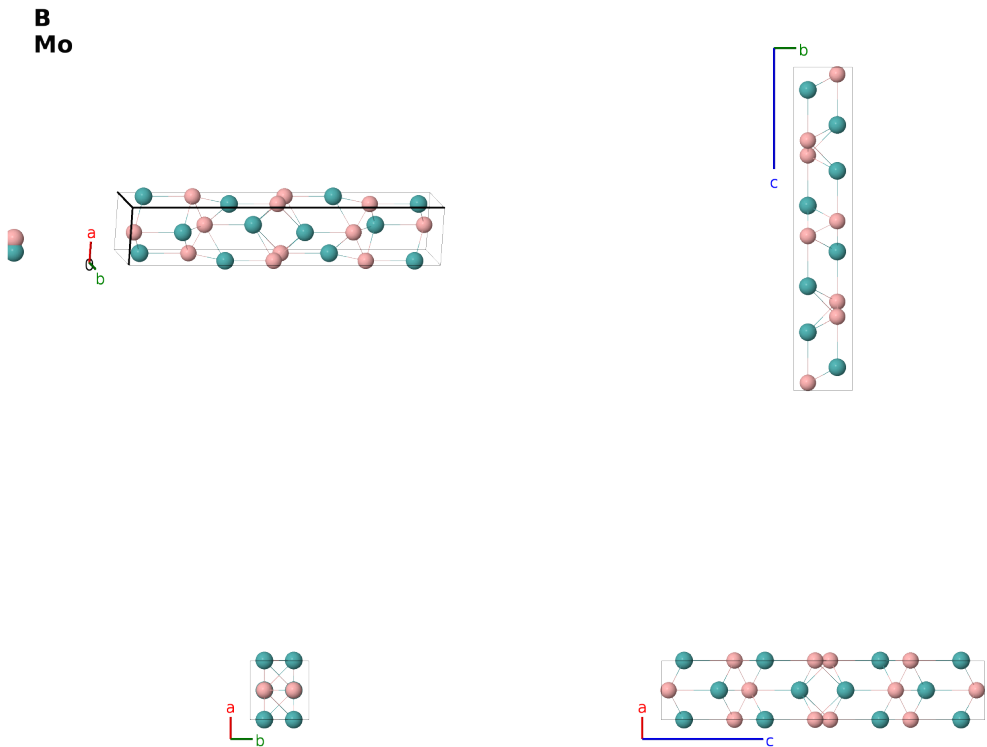

Prototype	BMo
AFLOW prototype label	AB_tI16_141_e_e-001
<i>Strukturbericht</i> designation	B_g
ICSD	24280
CCDC	1600325
Pearson symbol	tI16
Space group number	141

Space group symbol $I4_1/amd$


AFLOW prototype command `aflow --proto=AB_tI16_141_e_e-001`
`--params=a, c/a, z1, z2`

Other compounds with this structure

BCr, BW, GaZr, B₅Re₃V₂, Co₃Er₅Ni₂, Ga₃Hf₂Sc

Body-centered Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= -\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} - \frac{1}{2}c\hat{\mathbf{z}}\end{aligned}$$

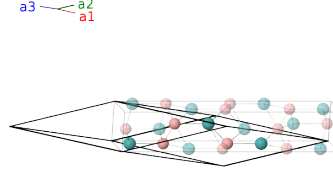

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \left(z_1 + \frac{1}{4}\right) \mathbf{a}_1 + z_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{y}} + cz_1\hat{\mathbf{z}}$	(8e)	B I
$\mathbf{B}_2$	$= z_1 \mathbf{a}_1 + \left(z_1 + \frac{1}{4}\right) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + c\left(z_1 - \frac{1}{4}\right)\hat{\mathbf{z}}$	(8e)	B I
$\mathbf{B}_3$	$= -\left(z_1 - \frac{3}{4}\right) \mathbf{a}_1 - z_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}a\hat{\mathbf{y}} - cz_1\hat{\mathbf{z}}$	(8e)	B I
$\mathbf{B}_4$	$= -z_1 \mathbf{a}_1 - \left(z_1 - \frac{3}{4}\right) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{4}a\hat{\mathbf{y}} - c\left(z_1 - \frac{1}{4}\right)\hat{\mathbf{z}}$	(8e)	B I
$\mathbf{B}_5$	$= \left(z_2 + \frac{1}{4}\right) \mathbf{a}_1 + z_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{y}} + cz_2\hat{\mathbf{z}}$	(8e)	Mo I
$\mathbf{B}_6$	$= z_2 \mathbf{a}_1 + \left(z_2 + \frac{1}{4}\right) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + c\left(z_2 - \frac{1}{4}\right)\hat{\mathbf{z}}$	(8e)	Mo I
$\mathbf{B}_7$	$= -\left(z_2 - \frac{3}{4}\right) \mathbf{a}_1 - z_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}a\hat{\mathbf{y}} - cz_2\hat{\mathbf{z}}$	(8e)	Mo I
$\mathbf{B}_8$	$= -z_2 \mathbf{a}_1 - \left(z_2 - \frac{3}{4}\right) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{4}a\hat{\mathbf{y}} - c\left(z_2 - \frac{1}{4}\right)\hat{\mathbf{z}}$	(8e)	Mo I

References

- [1] R. Kiessling, *The Crystal Structure of Molybdenum and Tungsten Borides*, Acta Chem. Scand. **1**, 893–916 (1947), doi:10.3891/acta.chem.scand.01-0893.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017