

Vysotskite (PdS, *B34*) Structure: AB_tP16_84_cej_k-001


This structure previously used the label(s) **AB_tP16_84_cej_k**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/KXWJ>

https://aflow.org/prototype-encyclopedia/AB_tP16_84_cej_k-001

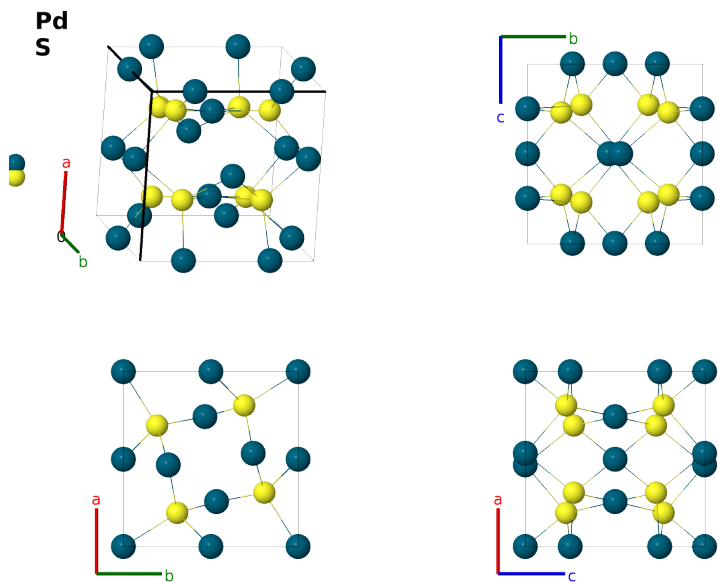

Prototype	PdS
AFLOW prototype label	AB.tP16.84.cej_k-001
<i>Strukturbericht</i> designation	<i>B34</i>
Mineral name	vysotskite
ICSD	22429
CCDC	2185340
Pearson symbol	tP16
Space group number	84
Space group symbol	$P4_2/m$
AFLOW prototype command	<code>aflow --proto=AB_tP16_84_cej_k-001</code> <code>--params=a, c/a, x₃, y₃, x₄, y₄, z₄</code>

Other compounds with this structure


PdSe, (Pt, Pd, Ni)S (braggite)

Simple Tetragonal primitive vectors

$$\mathbf{a}_1 = a \hat{\mathbf{x}}$$

$$\mathbf{a}_2 = a \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = c \hat{\mathbf{z}}$$

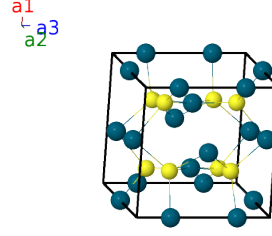

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2} a \hat{\mathbf{y}}$	(2c)	Pd I
$\mathbf{B}_2$	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} c \hat{\mathbf{z}}$	(2c)	Pd I
$\mathbf{B}_3$	$= \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4} c \hat{\mathbf{z}}$	(2e)	Pd II
$\mathbf{B}_4$	$= \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4} c \hat{\mathbf{z}}$	(2e)	Pd II
$\mathbf{B}_5$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2$	$=$	$ax_3 \hat{\mathbf{x}} + ay_3 \hat{\mathbf{y}}$	(4j)	Pd III
$\mathbf{B}_6$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2$	$=$	$-ax_3 \hat{\mathbf{x}} - ay_3 \hat{\mathbf{y}}$	(4j)	Pd III
$\mathbf{B}_7$	$= -y_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ay_3 \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(4j)	Pd III
$\mathbf{B}_8$	$= y_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ay_3 \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(4j)	Pd III
$\mathbf{B}_9$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + ay_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8k)	S I
$\mathbf{B}_{10}$	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - ay_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8k)	S I
$\mathbf{B}_{11}$	$= -y_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-ay_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} + c \left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8k)	S I
$\mathbf{B}_{12}$	$= y_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$ay_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + c \left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8k)	S I
$\mathbf{B}_{13}$	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - ay_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8k)	S I
$\mathbf{B}_{14}$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + ay_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8k)	S I
$\mathbf{B}_{15}$	$= y_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$ay_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} - c \left(z_4 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(8k)	S I
$\mathbf{B}_{16}$	$= -y_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-ay_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} - c \left(z_4 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(8k)	S I

References

- [1] N. E. Brese, P. J. Squattrito, and J. A. Ibers, *Reinvestigation of the structure of PdS*, Acta Crystallogr. Sect. C **41**, 1829–1830 (1985).

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017