

Pa (A_a) Structure: A_tI2_139_a-002


This structure previously used the label(s) **A.tI2.139.a.alpha-Pa**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/YF8N>

https://aflow.org/prototype-encyclopedia/A.tI2_139_a-002

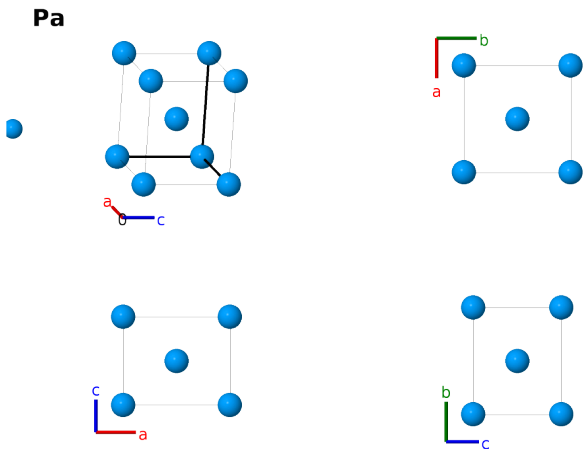

Prototype	Pa
AFLOW prototype label	A_tI2_139_a-002
<i>Strukturbericht</i> designation	A_a
ICSD	648333
CCDC	1763161
Pearson symbol	tI2
Space group number	139
Space group symbol	$I4/mmm$
AFLOW prototype command	<code>aflow --proto=A_tI2_139_a-002 --params=a,c/a</code>


- This is an example of a body-centered tetragonal (bct) lattice, a distortion of the bcc lattice.
- A_6 and A_a structures have the same AFLOW prototype label, A_tI2.139.a. They are generated by the same symmetry operations with different sets of parameters (**--params**) specified in their corresponding CIF files. When $c/a = \sqrt{2/3} \approx 0.861$ the coordination number of this system is 10. In Pa the c/a ratio is 0.823.
- We take our data from (Zachariasen, 1959), but the ICSD entry is from the later work of (Benedict, 1982).

Body-centered Tetragonal primitive vectors

$$\mathbf{a}_1 = -\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}}$$

$$\mathbf{a}_2 = \frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}}$$

$$\mathbf{a}_3 = \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} - \frac{1}{2}c\hat{\mathbf{z}}$$

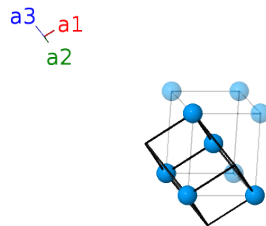

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(2a) Pa I

References

- [1] W. H. Zachariasen, *On the crystal structure of protactinium metal*, Acta Cryst. **12**, 698–700 (1959), doi:10.1107/S0365110X59002043.
- [2] U. Benedict, J. C. Spirlet, C. Doufour, I. Birkel, W. B. Holzapfle, and J. R. Petersen, *X-ray diffraction study of protactinium metal to 53 GPa*, J. Magn. Magn. Mater. **29**, 287–290 (1982), doi:10.1016/0304-8853(82)90252-9.

Found in

- [1] J. Donohue, *The Structures of the Elements* (Robert E. Krieger Publishing Company, New York, 1974).

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017