

β -Sn (A5) Structure: A_tI4_141_a-001


This structure previously used the label(s) **A.tI4.141.a**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/2BUF>

https://aflow.org/prototype-encyclopedia/A_tI4_141_a-001

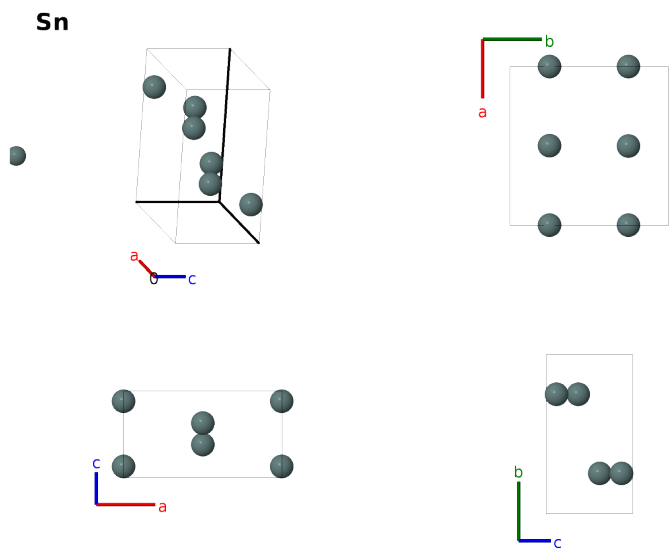

Prototype	Sn
AFLOW prototype label	A_tI4_141_a-001
<i>Strukturbericht</i> designation	A5
ICSD	52486
CCDC	1617232
Pearson symbol	tI4
Space group number	141
Space group symbol	$I4_1/amd$
AFLOW prototype command	<code>aflow --proto=A_tI4_141_a-001 --params=a,c/a</code>

Other compounds with this structure


β -Ge

- When $c/a = \sqrt{2}$ this structure is equivalent to diamond (A4).

- The binary version of this structure is the GaSb (II) structure.

Body-centered Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= -\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} - \frac{1}{2}c\hat{\mathbf{z}}\end{aligned}$$

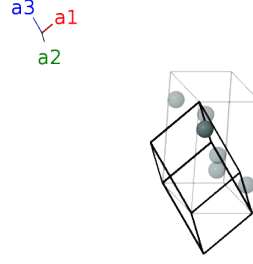

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{7}{8}\mathbf{a}_1 + \frac{1}{8}\mathbf{a}_2 + \frac{3}{4}\mathbf{a}_3$	$=$	$\frac{3}{4}a\hat{\mathbf{y}} + \frac{1}{8}c\hat{\mathbf{z}}$	(4a)	Sn I
$\mathbf{B}_2$	$= \frac{1}{8}\mathbf{a}_1 + \frac{7}{8}\mathbf{a}_2 + \frac{1}{4}\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{4}a\hat{\mathbf{y}} + \frac{3}{8}c\hat{\mathbf{z}}$	(4a)	Sn I

References

- [1] V. T. Deshpande and D. B. Sirdeshmukh, *Thermal Expansion of Tetragonal Tin*, Acta Cryst. **14**, 355–356 (1961), doi:10.1107/S0365110X61001212.

Found in

- [1] M. Winter, *Tin: crystal structures* (1993-2022). WebElements: the periodic table on the WWW, The University of Sheffield and WebElements Ltd, UK.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017